

Article

Preparation of Fe-Based MOFs Composite as an Adsorptive Photocatalyst with Enhanced Photo-Fenton Degradation under LED Light Irradiation

Patrick Armando ¹, Valentino Bervia Lunardi ¹, Felycia Edi Soetaredjo ¹, Jindrayani Nyoo Putro ¹, Shella Permatasari Santoso ¹, Christian Julius Wijaya ¹, Jenni Lie ¹, Wenny Irawati ¹, Maria Yuliana ¹, Hardy Shuwanto ², Hairus Abdullah ², I Gede Wenten ³ and Suryadi Ismadji ^{1,*}

¹ Department of Chemical Engineering, Widya Mandala Surabaya Catholic University, Kalijudan 37, Surabaya 60114, Indonesia

² Department of Industrial Engineering, Universitas Prima Indonesia, Medan 20117, Indonesia

³ Department of Chemical Engineering, Institute of Technology Bandung (ITB), Jl. Ganesha 10, Bandung 40132, Indonesia

* Correspondence: suryadiismadji@yahoo.com; Tel.: +62-31-3891264



Citation: Armando, P.; Lunardi, V.B.; Edi Soetaredjo, F.; Putro, J.N.; Santoso, S.P.; Wijaya, C.J.; Lie, J.; Irawaty, W.; Yuliana, M.; Shuwanto, H.; et al. Preparation of Fe-Based MOFs Composite as an Adsorptive Photocatalyst with Enhanced Photo-Fenton Degradation under LED Light Irradiation. *Sustainability* **2022**, *14*, 10685. <https://doi.org/10.3390/su141710685>

Academic Editor: Ning Yuan

Received: 28 June 2022

Accepted: 24 August 2022

Published: 27 August 2022

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

Abstract: In this study, a novel MIL-100(Fe)@TiO₂ composite was synthesized and used as the adsorbent to remove Rhodamine B from synthetic wastewater through adsorption and photocatalytic degradation. The composite was synthesized successfully using solvothermal methods. MIL-100(Fe)@TiO₂ composite has excellent adsorption and photodegradation capability for Rhodamine B removal. The reusability of the materials was observed, with the conclusion that the material still had good adsorption and photocatalytic performance after five cycles of consecutive experiments. The adsorption isotherm, kinetic, and thermodynamic studies of the removal of Rhodamine B were also conducted. The Langmuir model represented the adsorption equilibrium data better than other models. The kinetics of adsorption of Rhodamine B was presented well by pseudo-first-order. The thermodynamic study verified that the physisorption mechanism was more dominant than chemisorption. The addition of Fenton was also proven to be successful in increasing the photocatalytic abilities of the synthesized materials.

Keywords: metal–organic framework; photocatalytic degradation; thermodynamic; composite

1. Introduction

An emerging three-dimensional porous crystalline framework class, metal–organic frameworks (MOFs), exhibits ordered pore size and surface area, which is beneficial for catalytic application [1]. MOF outperforms conventional photocatalytic semiconductor materials in several factors such as framework versatility, huge surface area, and more significant void volumes. Currently, MOFs have been widely utilized as novel types of photocatalysts. This is due to the availability of electrons to be excited from the highest occupied molecular orbital (HOMO) to the lowest unoccupied molecular orbital (LUMO) due to LMCT (ligand-to-metal charge transfer), MLCT (metal-to-ligand charge transfer), and π - π^* transition in aromatic rings' properties when exposed to light irradiation [2]. Fe-based MOFs presented as high-grade photocatalysts among constructed MOFs due to their intrinsic optical absorbance, stability, inherent optical responsiveness, and low-cost synthesis [3]. Moreover, they have been demonstrated to be effective heterogeneous photo-Fenton-like, to produce OH radicals for the degradation of organic pollutants. However, the poor adsorption ability towards dye molecules [4,5] and low efficiency of excitation electron production and MOFs dye separation, contribute to limited efficiency in the photocatalytic system [6,7]. Therefore, a pristine MOFs photocatalyst cannot provide sufficient catalytic degrading efficiency and stability.

In recent years, the plausible strategy of improving MOFs photocatalytic activity was proven by incorporating semiconductors into MOFs. Amid a wide inorganic semiconductor selection, TiO_2 @MOFs surpass their counterparts in terms of a synergistic impact of high adsorption and efficient charge excitation and transfer. For instance, Huang et al. [8] reported that the impregnation of N- TiO_2 nanoparticles on MIL-100 (Fe) provides a great synergistic effect through electron-hole recombination restriction, along with suitable pore size and high surface area for promoting the photocatalytic reaction for methylene blue degradation [8]. In another study, He et al. [9] introduced MIL-100 (Fe) on the P-25 matrix to extend the light absorption ability to the visible region for efficiency degradation improvement against heavy metals [9]. Moreover, Liu et al. [10] engineered a hierarchical sandwich consisting of TiO_2 nanosheets and porous MIL-100 (Fe) to improve composite adsorption ability and limit the recombination of photo-generated e^-/h^+ pairs to promote the photocatalytic activity against methylene blue under visible light irradiation. The interfaces between TiO_2 semiconductors and MOFs provide many suitable sites for photo-generated electron transition, which significantly speeds up electron transfer and reduces electron-hole recombination. Additionally, the aggregation tendency of pristine TiO_2 can also be overcome by anchoring the MIL-100(Fe) on the TiO_2 surface. However, no study exploits the possibility of TiO_2 anatase for MIL-100(Fe) composite. Based on the structural configuration, TiO_2 anatase provides a unique structure with numerous defects that can confine high oxygen content for electron confinement [11].

In this study, we prepared novel photocatalyst Fe-based MOFs (MIL-100(Fe)) grown on the TiO_2 anatase surface to enhance the adsorption and photocatalytic degradation of dyes in the assistance of H_2O_2 and visible light. This paper selected rhodamine B (RhB) as a target emerging organic pollutant, to evaluate the adsorption and photo-Fenton performance of MIL-100(Fe)@ TiO_2 . Several adsorption isotherm and kinetic models were utilized to provide the insight mechanism of adsorption of RhB on the composites. Meanwhile, several process parameters such as catalyst ratio, catalyst dosage, and H_2O_2 content, which were co-existing inorganic anions on photo-Fenton degradation of RhB, were evaluated with an additional study regarding the stability and recyclability performance of MIL-100(Fe)@anatase TiO_2 . A plausible mechanism for photocatalytic degradation of RhB via LED irradiation by MIL-100(Fe)@ TiO_2 has been proposed.

2. Materials and Methods

2.1. Chemicals

The chemicals used in this study were ferric nitrate hexahydrate ($\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$) (CAS:7782-61-8; 99.95% purity trace metal basis), 1,3,5-Benzene Tricarboxylic Acid (H_3BTC) (CAS: 554-95-0; 98%), Titanium (IV) oxide (TiO_2) (CAS: 1317-70-10) anatase grade, 99.8% trace metal basis), rhodamine B ($\text{C}_{28}\text{H}_{31}\text{ClN}_2\text{O}_3$) (CAS:548-62-9; HPLC standard $\geq 95\%$ anhydrous basis), isopropyl alcohol (IPA) (CAS:67-63-0; ACS reagent $\geq 99.5\%$), *p*-benzoquinone ($\text{C}_6\text{H}_4\text{O}_2$) (CAS:106-51-4; reagent grade $\geq 99.5\%$), carbon tetrachloride (CCl_4) (CAS: 56-23-5; reagent grade $\geq 99.9\%$) and ammonium oxalate monohydrate ($(\text{NH}_4)_2\text{C}_2\text{O}_4 \cdot \text{H}_2\text{O}$) (CAS:106-51-4; ACS reagent $\geq 99\%$). All chemicals were procured from Sigma Aldrich, Singapore, and were subsequently used without additional purification.

2.2. Fabrication of MIL-100 (Fe)@ TiO_2 Composite

Different molar ratios of TiO_2 : $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ were used to synthesize MIL-100 (Fe)@ TiO_2 photocatalysts. The $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ solution concentration and mass of trimesic acid were maintained at 63.31 mmol/L and 1225 mg. The theoretical amount of anatase TiO_2 for different MIL-100 (Fe)@ TiO_2 combinations was calculated according to the mole ratio of 3:0.7, 3:1.4, and 3:2.4 ($\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$: TiO_2). The as-synthesized photocatalysts were named MxTy, where x and y correspond to the $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$: TiO_2 mole ratio of 3:0.7, 3:1.4, and 3:2.4 (for example, M₃T_{0.7} defines the mole ratio 3:0.7 between $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ and TiO_2). For the synthesis, 0.05, 0.1, and 0.2 g of anatase TiO_2 were added to 63.31 mmol/L of $\text{Fe}(\text{NO}_3)_3 \cdot 9\text{H}_2\text{O}$ solution, followed by mixing and heating at 368.15 K for 120

min. Then, the powders were acquired through multiple washes with DI water and centrifugation for iron residue removal. Subsequently, the powders were re-immersed with 20 mL of DI water and 1.25 g H₃BTC and mixed for 1 h. After 15 min of mixing, the mixture was placed into a Teflon autoclave and heated at 423.15 K for 12 h. The resultant light orange powders were isolated from the autoclave and dispersed in ethanol at 353.15 K for 3 h for H₃BTC residue removal. Eventually, the as-synthesized composite was isolated and dried at 333.15 K overnight. The resulting composite was defined as M₃T_{0.7}, M₃T_{1.4}, and M₃T_{2.4}, respectively.

As the control material, the pristine MIL-100 (Fe) was also fabricated through hydrothermal synthesis as reported elsewhere, with slight modifications (He et al., 2019). Initially, Fe(NO₃)₃·9H₂O and H₃BTC were dissolved in deionized water with additional HNO₃ in the mixture with an overall mole ratio of (Fe(NO₃)₃·9H₂O:H₃BTC:HNO₃:H₂O = 3.57:2.4:9.02:200). Subsequently, the mixture was magnetically stirred for 1 h, and placed on a Teflon-lined stainless-steel autoclave for isothermal heating at 423.15 K for 12 h. Afterward, the autoclave was naturally cooled to room temperature. Then, the light orange powder was collected through two-step purifications by water and ethanol at 333.15 K for 3 h to remove unreacted reactants. Eventually, the product pristine MIL-100(Fe) was dried overnight at 373.15 K. The synthesis steps are graphically presented in Figure 1.

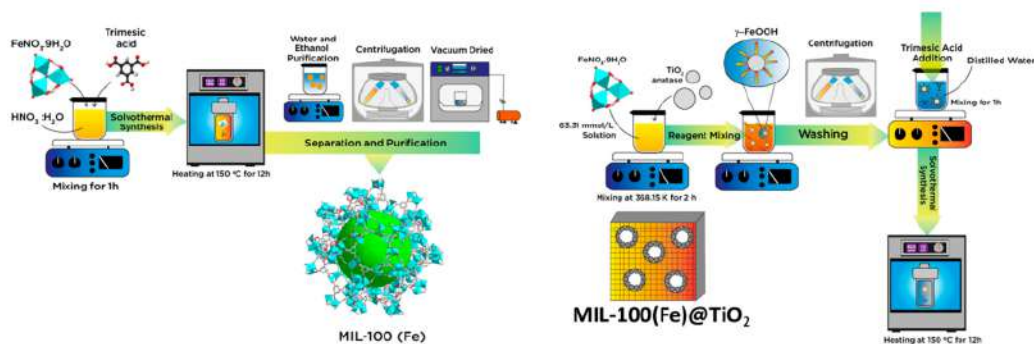


Figure 1. Synthesis Steps of MIL-100(Fe) (left) and MxTy Composites (right).

2.3. Characterization

The sample phase purity was analyzed through XRD by a Bruker D2 Phaser diffractometer equipped with a Cu K α radiation source ($\lambda = 0.15406$ nm). XRD patterns were measured in the 2θ range of 10° – 80° with a scan rate of $0.05^{\circ}/s$. The morphological and topological structure of the composite was produced by SEM (JEOL JSM-6500F field emission SEM) at an accelerating voltage of 15.0 kV and a working distance of 9.7 mm. Before the SEM analysis, all solid samples were coated with a thin layer of platinum. The Micromeritics ASAP 2020 analyzer measured N₂ sorption isotherms at 77 K, and the surface area and pore diameter distribution were calculated using Brunauer–Emmett–Teller (BET) and Barrett–Joyner–Halenda (BJH) models. Before the measurements, the samples were initially degassed for 12 h at 200°C in a vacuum atmosphere. The 209 F3Tarsus measured thermogravimetric analysis (TGA) under air at a heating rate of $10^{\circ}\text{C}/\text{min}$ to 600°C . X-ray photoelectron spectroscopy (XPS) was utilized for chemical state elements of MIL-100 (Fe)@TiO₂ analysis with a VG ESCA Scientific Theta Probe Spectrometer with Al K α (1486.6 eV) source and 15–400 mm X-ray spot size, operated at 3 kV and 1 mA. The UV diffuse reflectance spectra (DRS) were recorded using a Jasco V-670 UV-visible-near IR spectrophotometer with barium sulfate (BaSO₄) as the reflectance standard throughout the 200–800 nm wavelength range. Energy-dispersive X-ray spectrometry (EDS) equipped with TEM was used to perform element mapping and atomic composition analysis over the regions of interest. On Bio-Logic Science Instruments with EC-Lab[®] software, a three-electrode cell with a working electrode, a Pt counter electrode, and a standard Ag/AgCl reference electrode were used to analyze transient photocurrent

density. A solution containing 0.5 mol/L Na_2SO_4 served the electrolyte. Meanwhile, electrochemical impedance spectra (EIS) were also measured using Bio-Logic Science Instruments with EC-Lab[®] software. Photoluminescence (PL) spectrum was procured through a Jasco V-670 UV-visible-near IR spectrophotometer (Tokyo, Japan).

2.4. Adsorption and Degradation Photocatalytic Experiments

The current study examined the adsorption/photocatalytic degradation ability of MIL-100 (Fe)@ TiO_2 and MIL-100 (Fe) through RhB removability from an aqueous system. The adsorption experiment was carried out in the absence of LED light (50 W; 300–800 nm), whereas photocatalytic degradation was conducted in the presence of an LED lamp. The initial and equilibrium of RB concentrations were analyzed by monitoring the adsorption intensity at $\lambda = 553$ nm using a UV-visible spectrophotometer (UV-2550, Shimadzu). The adsorption and photocatalytic degradation studies were performed under several conditions to investigate their important effects during the adsorption/photocatalytic degradation process. Those effects/parameters are as follows:

- Adsorption kinetic study: A series of RhB solutions with an initial concentration of 100 ppm and a volume of 50 mL were prepared. After that, 50 mg of adsorbent was added each prepared solution. The adsorption was carried out under neutral pH and a shaking water bath at room temperature. The final concentration of RhB was measured at time intervals of 5 min.
- Adsorption isotherm study: A series of RhB solutions with various initial concentrations of 10 to 600 ppm and volumes of 50 mL were prepared. Subsequently, 50 mg of adsorbent was added to each prepared solution. The adsorption was conducted in a shaking water bath at neutral pH and room temperature. The final concentration of RhB was measured after the equilibrium condition was achieved.
- Effect of adsorbent mass: The same procedure as in the kinetic and isotherm studies was employed to study the influence of adsorbent mass on the adsorption of RhB. The various adsorbent mass of 10 to 50 mg was used in this case.
- Effect of MIL-100(Fe) and TiO_2 ratio: In this case, the adsorption procedure was similar to that described above. MIL-100(Fe) with various TiO_2 ratios (3:0.7, 3:1.4, and 3:2.4) were used as the adsorbents.
- Effect of Fenton Addition: A similar adsorption procedure was employed, and before the adsorption took place, 1, 2, or 3 mL of H_2O_2 was added to the mixture.
- Reusability test: Post-adsorption–photocatalytic process, ± 0.5 g samples were immersed in 96% ethanol overnight, followed by washing three times until the solutions turned clear. The regenerated samples were used as the adsorbents in the next adsorption–photocatalytic cycle.

The data acquired from the adsorption and photocatalytic degradation experiments were used to investigate the performance of MIL-100(Fe)@ TiO_2 towards RhB removal. The specific amount of RhB adsorbed and degraded at equilibrium condition was calculated by Equation (1) as follows:

$$q_e = \frac{(C_0 - C_e)}{m} \times V \quad (1)$$

where q_e is the number of adsorbed RhB at equilibrium (mg/g), C_0 and C_e are the initial and equilibrium concentration (mg/L) of RhB in the aqueous phase, respectively. V is the RhB solution volume (L), and m is the adsorbent dosage (g). The adsorption and degradation efficiency of RhB was measured through the following equation:

$$\eta = \left(1 - \frac{C}{C_0}\right) \times 100\% \quad (2)$$

where C_0 and C represent the initial and equilibrium RhB concentration at a specific time and temperature. For this experiment, all kinetics and isotherms models or equations are listed in Tables 1 and 2.

Table 1. Summary of non-linear kinetic models.

Kinetic Model	Non-Linear Equations	Parameters
Pseudo First Order (PFO)	$Q_t = Q(1 - e^{-k_1 t})$	Q_t (mg/g): adsorption capacity at various time, t $Q_{e,cal}$ (mg/g): calculated equilibrium capacity of adsorption k_1 (1/min): the rate constant of the PFO kinetic model
Pseudo Second Order (PSO)	$Q_t = \frac{Q_{e,cal}^2 k_2 t}{1 + Q_{e,cal} k_2 t}$	$Q_{e,cal}$ (mg/g): calculated equilibrium adsorption capacity k_2 (g/mg.min): the rate constant of PSO kinetic model h (mg/g.min) = $Q_{e,cal}^2 k_2$: the initial adsorption rate
Elovich	$Q_t = \frac{\ln(1 + (\alpha\beta t))}{\beta}$	α (mg/g.min): the initial adsorption rate β (g/mg): a parameter related to the activation energy for chemisorption and the extent of surface coverage
Intra-Particle Diffusion (IPD)	$Q_t = k_{IPD} t^{0.5} + C$	k_{IPD} (mg/g.min ^{0.5}): IPD constant rate C (mg/g): a constant that provides value regarding the thickness of the boundary layer.
First Order (FO) Kinetics	$C_t = C_0 \exp(-k_{1p} t)$	C_t (mg/L): final photocatalytic concentration C_0 (mg/L): initial photocatalytic concentration k_{1p} (1/min): the rate constant of FO kinetic model t (min): time of photocatalytic degradation
Second Order (SO) Kinetics	$1 - \frac{C_t}{C_0} = \frac{k_{2p} t}{1 + k_{2p} t}$	k_{2p} (L/mg.min): the rate constant of SO kinetic model t (min): time of photocatalytic degradation
Behnajadi, Modirshahla, and Ghanbary (BMC) Models	$1 - \frac{C_t}{C_0} = \frac{t}{m + bt}$	m (min): reciprocal of initial removal rate b (dimensionless): reciprocal theoretical maximum oxidation capacity

Table 2. Summary of non-linear isotherm models.

Isotherm Model	Non-Linear Equations	Technical Constant
Langmuir	$Q_e = \frac{Q_{m,cal} K_L C_e}{1 + K_L C_e}$	$Q_{m,cal}$ (mg/g): calculated maximum adsorption capacity K_L (L/mg): Langmuir isotherm constant $R_L = [1 / (1 + K_L C_e)]$; R_L (dimensionless); separation factor
Freundlich	$Q_e = K_F C_e^{1/n}$	K_F (mg/g)(L/g) ^{n} : Freundlich isotherm constant related to the adsorption capacity n ($1 < n < 10$): Degree adsorption favorability

Table 2. Cont.

Isotherm Model	Non-Linear Equations	Technical Constant
Redlich-Peterson (R-P)	$Q_e = \frac{K_{RP} C_e}{1 + a_{RP} C_e^g}$	K_{RP} (L/g): Redlich–Peterson isotherm constant a_{RP} (L/mg): Redlich–Peterson isotherm constant g ($0 < g < 1$): Redlich–Peterson isotherm binding constant
Sips	$Q_e = \frac{q_{ns} K_s C_e^{n_s}}{1 + K_s C_e^{n_s}}$	K_s (L/g): Sips isotherm model constant q_{ns} (mg/g): Sips isotherm maximum adsorption capacity n_s : Sips isotherm model exponent
Toth	$Q_e = \frac{Q_m T_0 C_e}{(K_{T_0} + C_e^{n_{T_0}})^{1/n_{T_0}}}$	$Q_m T_0$ (mg/g): maximum adsorption capacity K_{T_0} (mg/L): Toth isotherm constant n_{T_0} : Toth isotherm model exponent; $0 < n_{T_0} \leq 1$
Temkin	$Q_e = \frac{RT}{b_T} \ln K_T C_e$	b_T (J/mol): Temkin isotherm binding constant K_T (L/g): Temkin isotherm equilibrium binding constant R (8.314 J/mol.K): the ideal gas constant

9

3. Results and Discussion

3.1. Characterization

The crystal ¹⁰⁹ and phase purity of the obtained M_xT_y and TiO_2 (anatase) were measured using X-ray diffraction (XRD) (Figure 2). According to the XRD diffractograms, each synthesized M_xT_y resembled pristine MIL-100(Fe) peaks at 2θ angles of 11° and 20° , excluding $M_3T_{0.7}$. This resemblance also corresponded to the theoretical MIL-100(Fe) single-crystal XRD pattern based on CCDC 640,536 [12]. Other than MIL-100(Fe) peaks, the obtained M_xT_y also exhibited some key TiO_2 anatase peaks at 2θ angles of 28° , 36° , 56° , and 70° . These peaks corresponded to the (101), (211), and (204) crystal planes of TiO_2 (anatase) and fit the TiO_2 (anatase) simulated card (ICSD-50447) [13]. However, there was a slight shift within the observed peaks on the composite, compared with its pristine component. This can result from the increasing or decreasing band gaps, which is possible when two materials are combined. We can still safely assume that the peak shown on the composite was the peak of the pristine component because the shifting was consistent within each peak. With these two indicators present in the obtained M_xT_y , the XRD pattern provided sufficient evidence of TiO_2 characteristic peaks in the M_xT_y crystalline.

Furthermore, the SEM images were implemented further to clarify the structures and morphologies of the synthesized M_xT_y . As shown in Figure 3, the synthesized M_xT_y had an irregular triangle shape with a size in the range of nanoporous materials. According to SEM images, the syn ¹⁰⁵ sized particles tended to agglomerate and create an aggregate of materi ¹² affecting the adsorption and photocatalytic degradation performance. In addition, energy-dispersive X-ray spectroscopy (EDXS) was also employed to confirm the existence and distribution of each precursor inside the synthesized M_xT_y . The distribution of precursors inside the synthesized M_xT_y showed a match between the expected and actual metal ratios to TiO_2 (Figure 4).

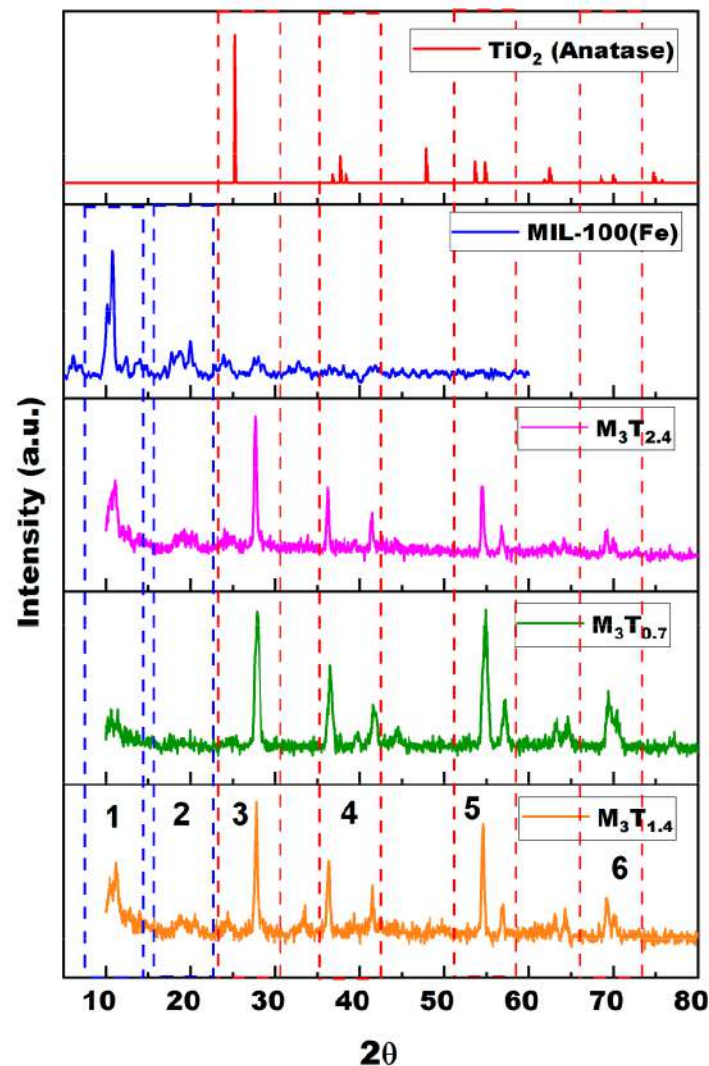


Figure 2. XRD patterns of pristine TiO_2 , MIL-100(Fe), and M_xT_y composites.

To further clarify the presence of each pristine MIL-100(Fe) and TiO_2 anatase inside the composite, the thermogravimetric analysis (TGA) was conducted, and is shown in Figure 5A. A weight loss around 200 °C was assigned to the removal of water molecules plus the desorption of ligand from the surfaces of the nanocrystals [10]. The decomposition of carboxylic acid was observed between 245–450 °C, which corresponded to the composite framework's collapse. When heated further, well over 450 °C, the TiO_2 anatase exhibited great thermal stability. In the $\text{M}_3\text{T}_{1.4}$ curve, we can see that the graph is more stable at high temperatures than pristine MIL-100(Fe), which indicates that the stability must come from the TiO_2 anatase presence within the $\text{M}_3\text{T}_{1.4}$. To study the pore structure of the synthesized materials, nitrogen sorption analysis was conducted, and is shown in Figure 5B. From the N_2 sorption result shown in Figure 5B, the TiO_2 anatase exhibited type II isotherm, and the composite isotherm exhibited type I and IV isotherm. The surface pore area was calculated, and is shown in Table 3. According to those results, the optimum ratio for MIL-100(Fe) and

TiO₂ to create the most significant surface area, which will benefit the application towards adsorption and photocatalytic degradation, was M₃T_{1.4}.

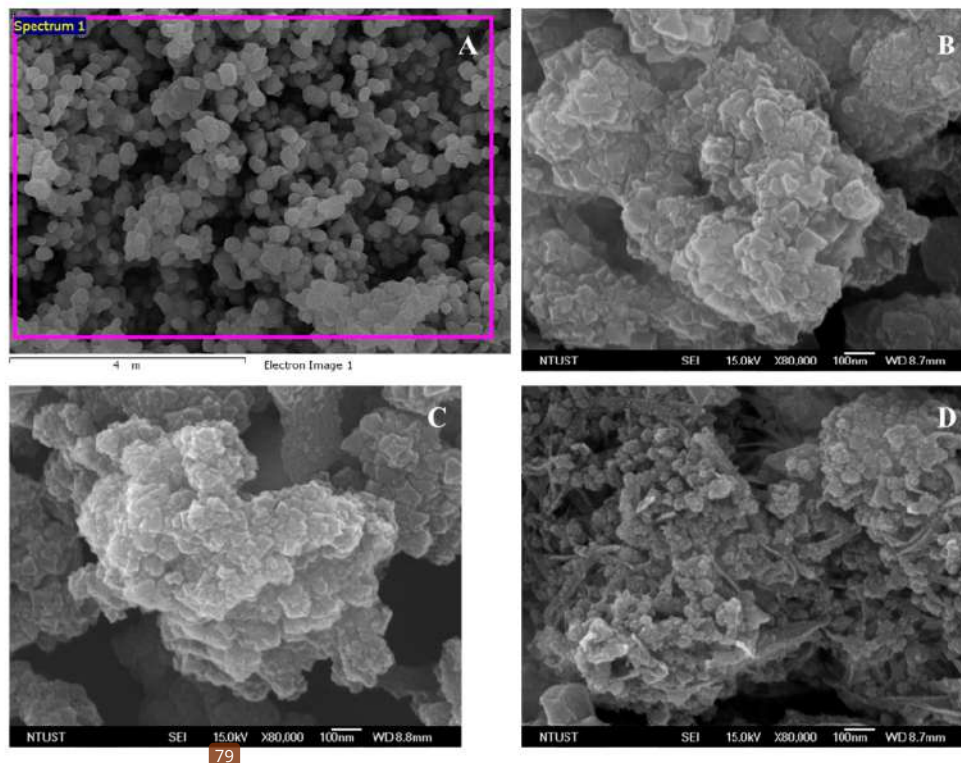


Figure 3. SEM images of (A) TiO₂ anatase; (B) M₃T_{0.7}; (C) M₃T_{1.4}; (D) M₃T_{2.4}.

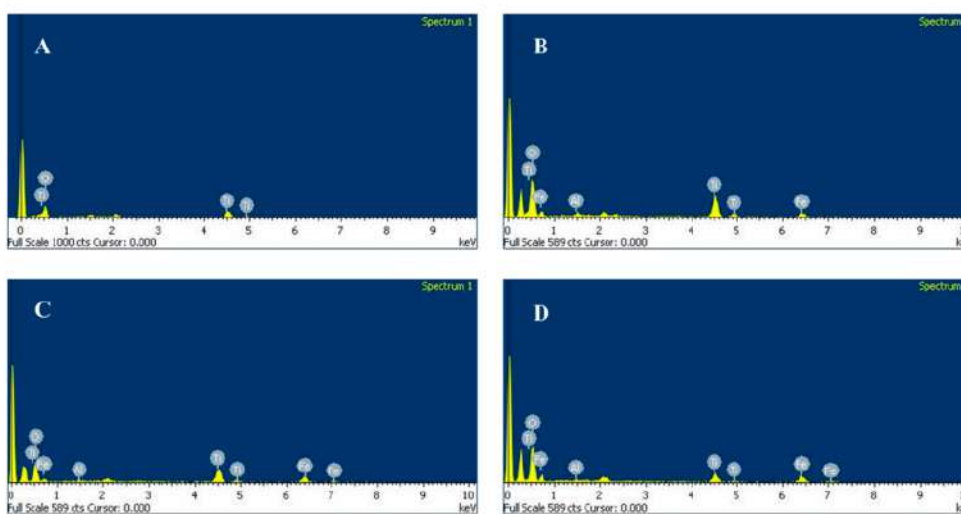


Figure 4. EDXS pattern of: (A) TiO₂ anatase; (B) M₃T_{0.7}; (C) M₃T_{1.4}; (D) M₃T_{2.4}.

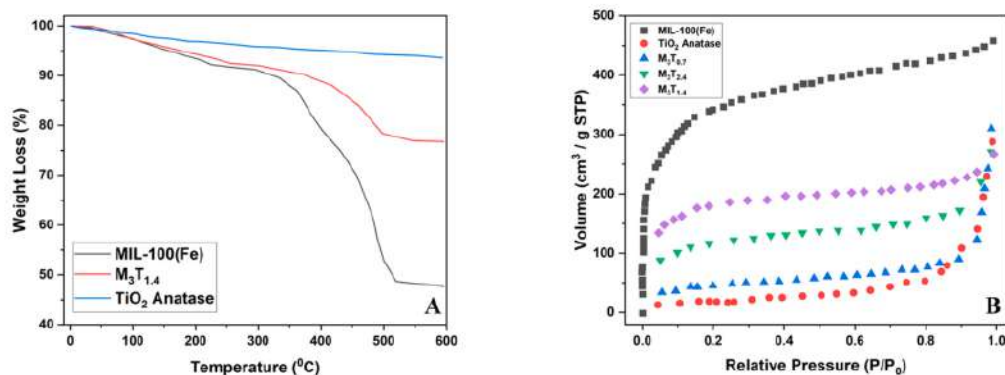


Figure 5. (A) TGA Curve and; (B) N_2 sorption isotherm.

Table 3. BET surface area results.

Materials	BET Surface (m ² /g)
MIL-100(Fe)	1576.4
$M_3T_{0.7}$	179.2
$M_3T_{1.4}$	450.7
$M_3T_{2.4}$	799.5
TiO_2 anatase	79.3

The photoluminescence spectra (PL) for each M_xT_y were investigated from 300 nm to 800 nm (Figure 6). Guo et al. [14] reported that the lower the PL intensity obtained, the more efficient the transfer of the photoinduced carriers and their generation inside the whole system. Distinctly, $M_3T_{1.4}$ showed the lowest PL curve, with $M_3T_{2.4}$ showing the highest PL curve. This phenomenon shows that $M_3T_{1.4}$ provided significantly enhanced separation efficiency and reduced recombination rate of the excited electron-hole pairs, the most suitable/profitable to use in the photocatalytic degradation system.

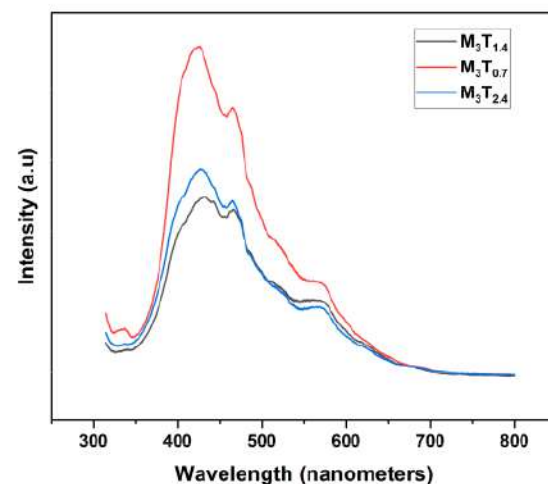


Figure 6. PL spectra of M_xT_y composites.

The stability of the synthesized M_xT_y under visible light irradiation was studied using the transient photocurrent tests. The experiments were recorded under visible light irradiation, which was switched on and off regularly. As shown in Figure 7, the photoexcited electrons that produced the photocurrent were observed when the light was turned on. The photo-generated carriers' better separation efficiencies and a longer lifetime is indicated by higher photocurrent density [14]. $M_3T_{1.4}$ exhibited higher photocurrent density than other ratios, indicating that $M_3T_{1.4}$ can provide good separation efficiencies and a longer photo-generated carrier's lifetime than other synthesized ratios.

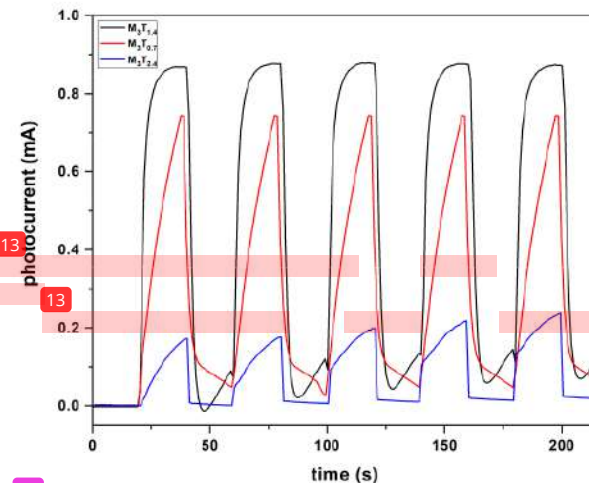


Figure 7. Transient photocurrent density spectra of M_xT_y composites.

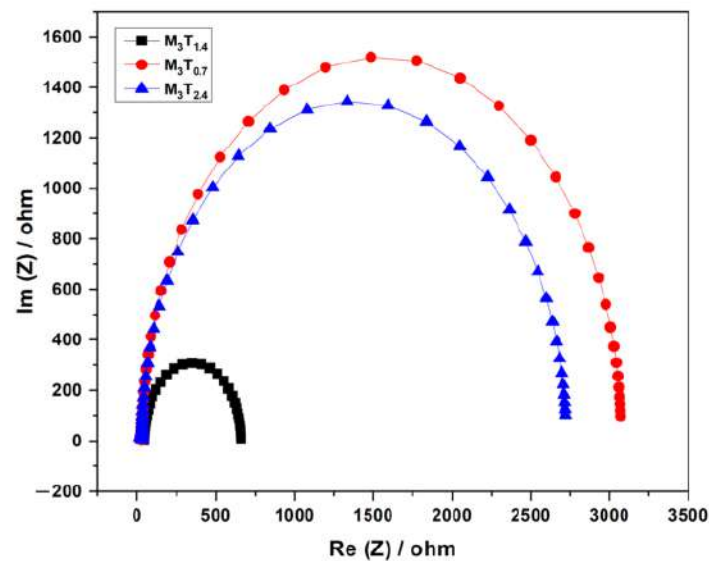


Figure 8. EIS spectra of M_xT_y composites.

The impedance of the photoanodes was used to examine the charge transport capability, and electron impedance spectra (EIS) tests were conducted. A smaller arc diameter at high frequency implies high efficient charge separation and electron transfer [14]. As shown in Figure 8, $M_3T_{1.4}$ also exhibited a smaller arc diameter than other M_xT_y , indicating efficient charge separation and electron transfer capability of the material compared with other M_xT_y . The EIS results were consistent with the PL and transient photocurrent tests, indicating the highest photocatalytic capability efficiency of the $M_3T_{1.4}$ under visible light irradiation.

The chemical bonding of MIL-100(Fe) and TiO_2 atoms was characterized using XPS (Figure 9). The full survey spectrum of XPS distinctly disclosed the existence of Fe, O, Ti, and C elements. The high-resolution spectra of O1s, Ti2p, and Fe2p are also shown in Figure 8. In the spectrum of O1s, peaks at 528.6, 530.3, and 531.7 eV were assigned to C=O bonding (carboxyl group in benzene tricarboxylic acid), O-Fe bond (ligand bonding with the metal), and Ti-O-Ti bond (from TiO_2 molecules) [10]. Peaks at 458.6 and 466.3 eV in the spectrum of Ti2p corresponded to Ti 2p_{3/2} and Ti 2p_{1/2}, respectively. The binding energy difference of 7.7 eV between Ti 2p_{3/2} and Ti 2p_{1/2} showed the chemical state of Ti^{4+} in MIL-100(Fe)/ TiO_2 materials [15]. In the Fe2p spectrum, two peaks were observed at 712.9 and 727.3 eV, which were assigned to Fe 2p_{3/2} and Fe 2p_{1/2}. Therefore, the chemical state of Fe(III) was present in MIL-100(Fe) [16]. Peaks at 284.6 eV and 288.9 eV in the spectrum of C1s corresponded to the benzene ring (from the benzene tricarboxylic acid) and a carboxyl group. XPS analysis provided sufficient evidence for the chemical interaction between MIL-100(Fe)/ TiO_2 molecules.

The optical absorption capability of synthesized M_xT_y was investigated using UV-Vis DRS. As seen in Figure 10, $M_3T_{1.4}$ exhibited a higher and broader spectrum than other M_xT_y , indicating that $M_3T_{1.4}$ can be considered an optimum metal-to- TiO_2 ratio for its ability to absorb lightwaves. The optical band gap of each M_xT_y was calculated using the Kubelka-Munk function versus the energy of absorbed light [17]. Figure 10 shows that the optical band gap of $M_3T_{1.4}$ was around 3.26 eV, $M_3T_{0.7}$ was around 3.67 eV, and $M_3T_{2.4}$ was around 4.16 eV. Figure 11 shows the Tauc plot obtained from UV-Vis DRS spectra of each precursor, as well each synthesized ratio.

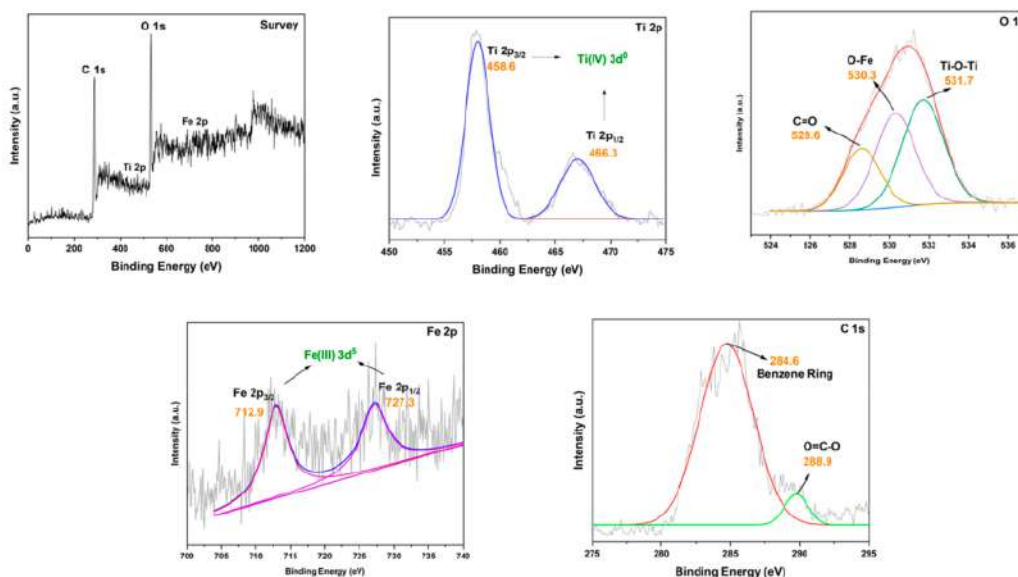


Figure 9. XPS spectra of M_xT_y .

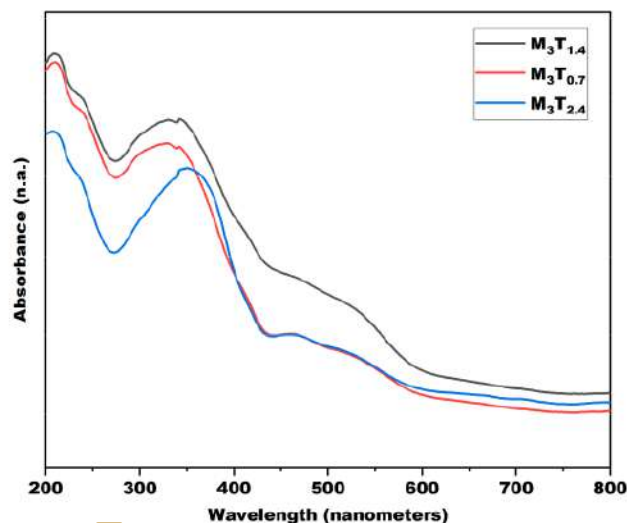


Figure 10. UV-Vis DRS spectra of M_xT_y composites.

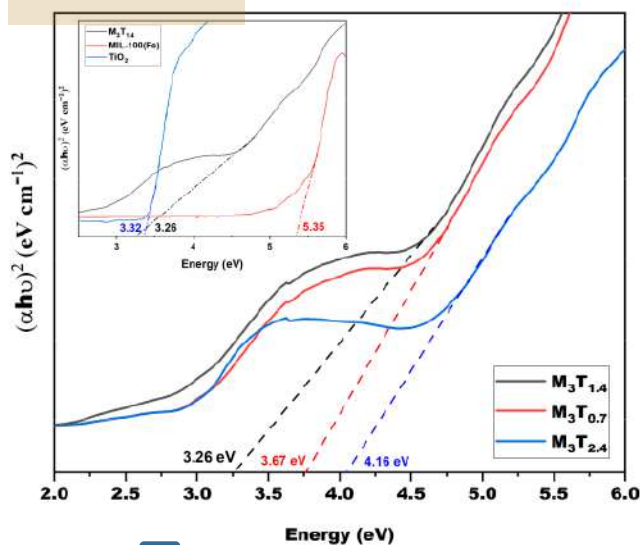


Figure 11. Tauc plot of UV-Vis DRS spectra composites.

The photocatalytic capability of composite materials was also compared with its precursors. The individual band gap of $M_3T_{1.4}$, which is gained from UV-Vis DRS, combined with the geometric mean of Mulliken electronegativity values of its constituent atoms, was used to calculate the conduction and valence band of materials using this empirical formula [13]:

$$E_{VB} = X - E_e + 0.5E_g \quad (3)$$

$$E_{CB} = E_{VB} - E_g \quad (4)$$

where variable "X" represents the Mulliken electronegativity of an element (5.81 eV for $24P_2$, 6.74 eV for MIL-100(Fe), and 6.69 eV for MIL-100(Fe)@ TiO_2), E_e is the energy of free electrons on the hydrogen scale with a value constant of 4.5 eV vs. NHE [18], and E_g

represents the sample's bandgap energy measured using UV-Vis DRS. Table 4 summarizes the values for E_g , E_{CB} , X , and E_{VB} of the composites and their precursors.

Table 4. Summary of electronegativity, X , band gap energy E_g (in eV), energy positions of band edges E_{CB} and E_{VB} (in eV) of composite and its precursors.

Materials	X (eV)	E_g (eV)	E_{CB} (eV)	E_{VB} (eV)
MIL-100(Fe)	6.74	5.35	−0.43	4.91
TiO ₂ anatase	5.81	3.32	−0.35	2.97
MIL-100(Fe)@TiO ₂ (M ₃ T _{1.4})	6.69	3.26	0.61	3.87

3.2. Adsorption Kinetics and Isotherm

Rhodamine B's (RhB) adsorption kinetics of M_xT_y were correlated using pseudo-first, pseudo-second, and Elovich models, while the Langmuir, Freundlich, Temkin, Sips, Toth, and Redlich–Peterson adsorption equations were used to represent the experimental adsorption data. The fitted pseudo-first kinetic models for M₃T_{0.7}, M₃T_{1.4}, and M₃T_{2.4} are shown in Figure 12A, while the fitted pseudo-second and Elovich models for M₃T_{1.4} are shown in Figure 12B. Based on the non-linear kinetic correlation shown in Table 5, pseudo-first-order kinetics represented the experimental data better than other kinetics equations. Figure 40 shows that the system reached equilibrium in approximately 60 min. Figure 12C shows the intra-particle diffusion model for studying the diffusion mechanism and its rate towards the RhB adsorption process. The non-linear curve between q_e and $t^{0.5}$ indicates that the adsorption occurred in multiple steps. The first stage involved the fast transfer from the solution to the surface of M_xT_y, which utilized previous isotherm models, driven by the electrostatic interactions (physical sorption) between the organic dyes and water molecules. The next step was a slower diffusion from the surface to the pore of the M_xT_y nanoparticles, which corresponded to the final equilibrium state of the adsorbate and adsorbent. The experimental adsorption isotherm data and fitting for Langmuir models towards pristine MIL-100(Fe), M₃T_{0.7}, M₃T_{1.4}, and M₃T_{2.4} are shown in Figure 13A, while the other fitted isotherm models for M₃T_{1.4} are shown in Figure 13B. Based on the non-linear isotherm correlation shown in Table 6, the Langmuir model isotherm represented the experimental data better than other isotherm equations, indicated by a higher correlation coefficient (R^2). It can also be seen that M₃T_{1.4} indicated the highest equilibrium adsorption capacity (q_e), compared with other composites.

According to Giles et al. [19], the classification of the isotherm plots in all experiments represents the L-curve (normal or Langmuir isotherm) with subclass 2. The L-curve frequently demonstrated the behavior of solute adsorption in an aqueous solution onto an adsorbent. In most Langmuir isotherm cases, the solute adsorption continuously increased along with the solute concentration and adsorption site availability, until the active sites reached their saturation capacity. This statement infers that the availability of the active site plays a significant role in determining the adsorbent's adsorption capacity. Therefore, it was rational for MIL-100 (Fe)@TiO₂ with the optimum mole ratio of 3:1.4 to have high adsorption capacity since it provided better adsorption accessibility of solute towards active sites (Table 3). In addition, the refinement of adsorption sites available through the structural porosity adjustment led to a rise in the affinity constant or Langmuir constant (K_L). This suggests that a strong affinity occurred between adsorbate and adsorbent [20]. Meanwhile, the plateau plots with subclass 2 were observed after a specific adsorption time. This phenomenon was caused by the adsorbent's monolayer saturation, resulting in the solute affinity towards the adsorption sites being lower than the solvent. In this case, increasing adsorption temperature negatively influenced the attachment of solute towards new sites after reaching its first saturation capacity. The increasing temperature decreased the adsorption capacity of M_xT_y (Figure 13C). As the temperature rose, the nature of the solute dye molecules' solubility increased, which further assisted the mobility and diffusion of RhB leaving the adsorption sites. This theory was consistent with the

adsorption data of RhB onto MIL-100 (Fe)@TiO₂, where the maximum saturation capacity (q_{max}) decreased along with the increase in temperature (Table 7), which indicated the adsorption was exothermic. t

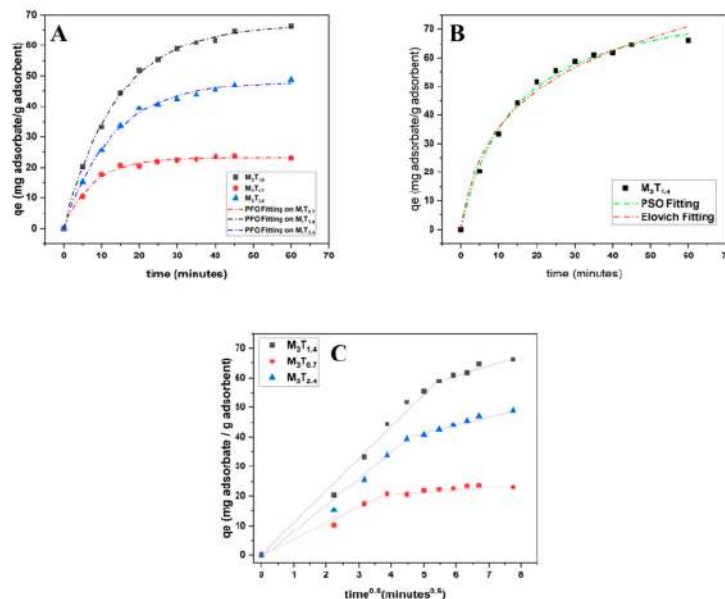


Figure 12. Adsorption kinetics models (A) each component towards PFO equation; (B) M₃T_{1.4} towards other kinetic models; (C) intra-particle diffusion models.

3.3. Thermodynamic Study

The thermodynamic system fundamentally evaluated the adsorption system to determine physisorption or chemisorption. Physisorption (known as physical adsorption) is controlled by relatively weak coordination through van der Waals forces, while chemisorption (or chemical adsorption) takes advantage of the sharing electron's ability of adsorbent and adsorbate to construct strong chemical bonding. Judging by the value of several thermodynamic parameters, such as the Gibbs energy change (ΔG°) and the enthalpy change (ΔH°), both physical and chemical adsorption can be evaluated. The thermodynamic parameters also determined the system behavior during the adsorption. For instance, the spontaneity of the system was determined based on the value of ΔG° (the adsorption process will not be favorable and non-spontaneous when the ΔG° exhibits a positive quantity, while it will be feasible and spontaneous with the negative value of ΔG°). Meanwhile, the value of ΔH° reflects whether the system is exothermic ($\Delta H^\circ < 0$) or endothermic ($\Delta H^\circ > 0$). The chemical adsorption was dominantly presented by the system with endothermic nature, which required a certain amount of energy from the surroundings to construct interaction. By contrast, the exothermicity system was indicated by the decrease in adsorption capacity with the increasing temperature; the system releases heat energy toward the surroundings. The ΔS° value also draws a significant aspect in determining the adsorbate distribution pattern at the solid/solution interface, whether it is less than zero ($\Delta S^\circ < 0$) or more randomly distributed ($\Delta S^\circ > 0$). In addition, the positive and negative values of ΔS° also correspond to adsorption's dissociative and associative mechanism.

Table 5. Parameters of kinetic models.

Adsorbents	Model	Parameters *		
		R^2	k_1	$Q_{e,cal}$
MIL-100(Fe)	PFO	0.9967	0.0769	58.3991
M ₃ T _{0.7}		0.9934	0.1297	23.1596
M ₃ T _{1.4}		0.9992	0.0717	66.6876
M ₃ T _{2.4}		0.9971	0.0775	48.1273
		R^2	k_{IPD}	C
MIL-100(Fe)	IPD	0.9844	10.7556	1.9822
		0.9825	3.8083	30.5665
M ₃ T _{0.7}		0.9712	4.9588	0.1858
		0.9559	1.3586	14.746
M ₃ T _{1.4}		0.9894	11.3210	1.4738
		0.9005	2.9697	43.558
M ₃ T _{2.4}		0.9805	8.5686	1.2118
		0.9404	3.6735	21.778
		R^2	$k_2 \times 10^4$	$Q_{e,cal}$
MIL-100(Fe)	PSO	0.9945	11.0122	73.0601
M ₃ T _{0.7}		0.9839	63.2139	26.7105
M ₃ T _{1.4}		0.9952	8.5068	84.3482
M ₃ T _{2.4}		0.9942	13.3000	60.1353
		R^2	α	β
MIL-100(Fe)	Elovich	0.9837	8.8664	0.0543
M ₃ T _{0.7}		0.9599	13.1702	0.2003
M ₃ T _{1.4}		0.9843	8.9117	0.0457
M ₃ T _{2.4}		0.9828	7.4064	0.0662

* Calculated based on non-linear fitting on Origin Pro 2021 Software (Northampton, MA, USA).

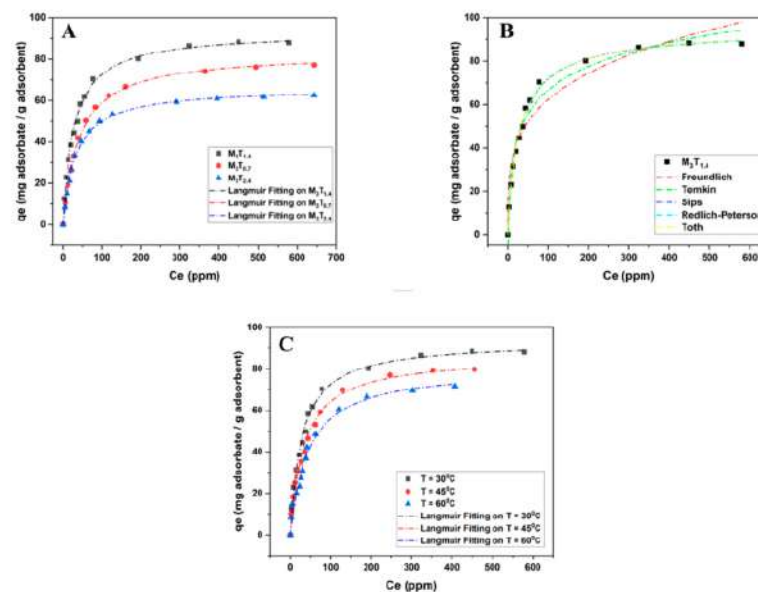


Figure 13. Adsorption isotherm models: (A) each component towards the Langmuir model; (B) $M_3T_{1.4}$ towards other isotherm models; (C) at different temperatures.

Table 6. Parameters of isotherm equations.

Adsorbents	Model	Parameters *			
		R^2	K_L	$Q_{max} (calc)$	
MIL-100(Fe)	Langmuir	0.9977	0.0344	58.9810	
M ₃ T _{1.4}		0.9944	0.0354	93.0977	
M ₃ T _{0.7}		0.9975	0.0243	83.1217	
M ₃ T _{2.4}		0.9977	0.0306	66.2711	
		R^2	K_F	n	
MIL-100(Fe)	Freundlich	0.9322	10.5269	3.5129	
M ₃ T _{1.4}		0.9282	18.9381	3.8696	
M ₃ T _{0.7}		0.9158	13.7269	3.5249	
M ₃ T _{2.4}		0.9118	12.6302	3.7898	
		R^2	K_{RP}	α_{RP}	g
MIL-100(Fe)	R-P	0.9968	2.0290	0.0349	0.9932
M ₃ T _{1.4}		0.9946	3.4787	0.0415	0.9827
M ₃ T _{0.7}		0.9975	2.0290	0.0349	0.9999
M ₃ T _{2.4}		0.9971	2.0155	0.0300	0.9939
		R^2	K_S	q_{ms}	n_s
MIL-100(Fe)	Sips	0.9988	0.0410	58.9019	0.9755
M ₃ T _{1.4}		0.9947	0.0464	95.9308	0.9004
M ₃ T _{0.7}		0.9999	0.0161	80.0316	1.1376
M ₃ T _{2.4}		0.9982	0.0392	63.8829	0.9181
		R^2	$Q_{m,To}$	K_{To}	n_{To}
MIL-100(Fe)	Toth	0.9973	58.2251	29.0698	0.9883
M ₃ T _{1.4}		0.9950	96.1932	15.9191	0.8679
M ₃ T _{0.7}		0.9975	83.1153	41.2046	0.9921
M ₃ T _{2.4}		0.9977	66.2678	32.6964	0.9993
	Temkin	R^2	b_T	K_T	
MIL-100(Fe)		0.9874	239.5997	0.5517	
M ₃ T _{1.4}		0.9789	159.7044	0.6830	
M ₃ T _{0.7}		0.9758	161.7385	0.3309	
M ₃ T _{2.4}		0.9719	211.4439	0.4610	

* Calculated based on non-linear fitting on Origin Pro 2021 Software (Northampton, Massachusetts, USA).

Table 7. Parameters of Langmuir equation at various temperatures.

T(K)	R^2	K_L	ρ (g/L)	$Q_{max} (calc)$
303.15	0.9944	0.0354	996.584	93.0977
318.15	0.9874	0.0293	991.003	86.1641
333.15	0.9837	0.0226	985.917	80.7086

89

The conventional way to determine the thermodynamic parameters of adsorption is based on the third principle of thermodynamic laws:

$$\Delta G^\circ = -RT \ln (K_c) \quad (5)$$

The correlation between ΔG° , ΔH° , and ΔS° can be written as follows:

$$\Delta G^\circ = \Delta H^\circ - T\Delta S^\circ \quad (6)$$

Substitution of Equation (5) into Equation (6) produces a well-known van 't Hoff equation which is widely used to obtain the thermodynamics parameters of adsorption:

$$\ln(K_c) = -\frac{\Delta H^\circ}{RT} + \frac{\Delta S^\circ}{R} \quad (7)$$

The calculation or determination of the thermodynamic equilibrium constant, K_c , is still under debate [21]. Various approaches have been proposed for that purpose; several directly use the parameters obtained from the fitting of the experimental adsorption data using adsorption isotherm equations as the equilibrium constant [22]. This approach neglects the dimensionality of K_c since the adsorption isotherm parameters usually have their units. Various researchers also developed or used other thermodynamic approaches that neglect the dimensionality of K_c to calculate the adsorption thermodynamics [23].

Several issues that need to be considered in determining the valid K_c and accurate thermodynamic parameters are:

- The thermodynamic equilibrium constant, K_c , should be dimensionless;
- The selection of adsorbate concentration is critical to determine which model could be used;
- The regression coefficient (R^2) of the van 't Hoff equation must be high and linear, and calculated based on temperature with kelvin units (K);
- The behavior of isotherms, experimental data, and thermodynamic parameters should be logical and consistent.

In recent studies, there have been two primary approaches to determining the thermodynamic equilibrium constant: (1) the distribution or partition coefficient model; (2) the isotherm adsorption model constant (the most common Langmuir constant). This study employed the partition coefficient model as the starting point for model development.

The partition model, which observes the adsorption system as the apportionment of adsorbate between solid and liquid phases, is an old-fashioned model for liquid-phase adsorption. Biggar and Cheung [24] proposed this model to evaluate the thermodynamic adsorption of picloram onto several soils. For this typical adsorption system, the chemical equation has been described as follows:



where $A_{(s)}$ is the adsorbate in the solid phase, while $A_{(l)}$ is the adsorbate in the liquid phase. The equilibrium parameter of Equation (8) can be written as follows:

$$K_p = \frac{[A_{(s)}]}{[A_{(l)}]} = \frac{C_s \gamma_s}{C_e \gamma_e} \quad (9)$$

where $[A_{(s)}]$ and $[A_{(l)}]$ are the activity of adsorbate in adsorbent and solution at equilibrium, respectively. Meanwhile, γ_s and γ_e are the activity coefficient of adsorbate on the adsorbent and in solution during equilibrium. C_s (mg/L) and C_e (mg/L) correspond to the adsorbate concentration on the adsorbent and in solution at equilibrium. In specific conditions, the value of the activity coefficient reached unity when nearly zero adsorbate concentration was observed, and Equation (9) becomes:

$$\lim_{C_s \rightarrow 0} \frac{C_s}{C_e} = \frac{a_s}{a_e} = K_p \quad (10)$$

In this model, the K_p value can be acquired by plotting $\ln(C_s/C_e)$ (y-axis) vs. C_e (x-axis) and extending the C_e value to zero, and the intersection with the vertical axis produces the value of K_p . The high value of the regression coefficient (R^2) should be obtained to obtain the valid value of K_p .

Khan and Singh proposed the distribution coefficient (K_d) based on the partition model [25]. The distribution coefficient can be written as follows:

$$K_d = \frac{Q_e}{C_e} \quad (11)$$

Q_e (mg/g) is the amount of adsorbate in the solid at equilibrium condition, while the symbol C_e (mg/L) represents the equilibrium concentration. This method obtains the K_d value similarly to Equation (10). As the distribution coefficient, K_d calculated from Equation (11) has a unit of L/mg. Furthermore, in an adsorption system, each value of Q_e corresponds to a value of C_e . At the high-medium to high value of C_e , in most adsorption systems, the value of Q_e does not increase linearly, and it becomes constant when a saturated condition is achieved. The inclusion of adsorption isotherm at medium and high equilibrium concentrations always results in a low value of the regression coefficient (R^2).

To obtain the value of K_d with a high R^2 , the value of Q_e should be linearly increased with C_e , and this condition can be achieved when the adsorption isotherm is linear. The linear part of the adsorption isotherm occurs when the equilibrium concentration is low or very low. Now consider the Langmuir equation as follows:

$$Q_e = Q_{max} \frac{K_L C_e}{1 + K_L C_e} \quad (12)$$

where Q_{max} (mg/g) is Langmuir's parameter representing the adsorbate's adsorption capacity, K_L (L/mg) is the adsorption affinity. At very low equilibrium concentration ($C_e \ll 1$), the Langmuir equation can be written as:

$$Q_e = Q_{max} \cdot K_L \cdot C_e \quad (13)$$

Equation (13) gives a linear correlation between Q_e and C_e , and:

$$\frac{Q_e}{C_e} = Q_{max} K_L \quad (14)$$

Substitution of Equation (14) to Equation (11) gives:

$$K_d = Q_{max} \cdot K_L \quad (15)$$

Here the unit of K_d obtained from Equation (15) is L/g. Several studies directly used the value of K_d as the equilibrium constant K_c (dimensionless constant) to obtain thermodynamic parameters of several adsorption systems. Since the unit L in K_d is the unit volume of solution, it can be easily converted into mass by multiplying with the density of solution ρ (g/L)

$$K_d = Q_{max} \cdot K_L \cdot \rho \quad (16)$$

The distribution coefficient calculated from Equation (16) is dimensionless. Equation (16), for the first time, was proposed by Milonjić [26] by taking the density of water to 1000.

$$K_d = Q_{max} \cdot K_L \cdot 1000 \quad (17)$$

The thermodynamics properties of RhB adsorption to the surface of MIL-100(Fe)@TiO₂ are given in Table 8. At all temperatures examined, the Gibbs free energy (ΔG°) for the adsorption of RhB was negative with a value lower than -20 kJ/mol, which indicated the spontaneous nature of RhB adsorption towards MIL-100(Fe)@TiO₂ and that physical adsorption controls the mechanism. Increasing temperature decreased the ΔG° value, implying that the

affinity of RhB onto MIL-100(Fe)@TiO₂ was diminished at higher temperatures. The negative ΔH° value (-16.74 kJ/mol) confirmed that adsorption was an exothermic process with the value of ΔH° under -21.9 kJ/mol, verifying that the physisorption mechanism was more dominant than chemisorption.

Table 8. Thermodynamic parameters of the adsorption of RhB on MIL-100(Fe)@TiO₂.

Temperature (K)	Thermodynamic Parameters				
	$\ln K_d$	ΔG°	ΔH°	ΔS°	R^2
303.15	8.0958	-20.4046	-16.7413	12.1974	0.9935
318.15	7.8238	-20.6947			
333.15	7.4964	-20.7636			

3.4. Effect of Variables on Photocatalytic Dye Adsorption—Degradation

3.4.1. Effect of Adsorbent Mass towards Adsorption

The effect of the adsorbent loading on the adsorption capacity was investigated in this study. As shown in Figure 14, the adsorption capacity towards RhB after 60 min increased when the adsorbent dose increased from 10 to 50 mg. This result indicated that more surface area and active sites were available with increasing adsorbent dosage in the adsorption system.

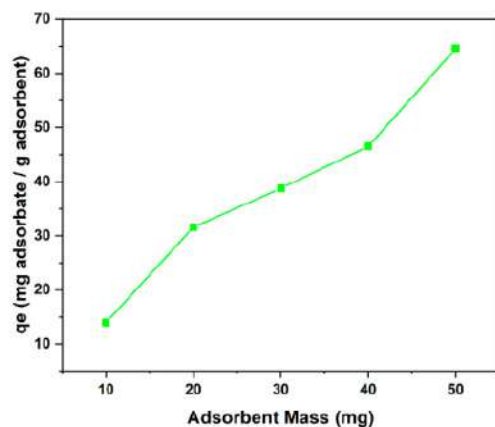


Figure 14. Effect of adsorbent mass towards RhB adsorption.

3.5. Effect of Adsorbent Ratio towards Photocatalytic Degradation

Different ratios of the MIL-100(Fe) and TiO₂ in the composite could impact the material's porosity, thus, impacting its transfer efficiency and accessibility of the active sites for photocatalytic degradation. This occurrence was studied by varying the mole ratio of TiO₂ (0.7; 1.4; and 2.4) incorporated into the constant amount of MIL-100(Fe) (denoted as M₃T_{0.7}; M₃T_{1.4}; and M₃T_{2.4}). The suitable amount of TiO₂ inside the composite could enhance the photoreactivity of the composite by increasing the specific surface area and promoting charge transfer [13]. The results of this study are shown in Figure 15. As shown in the figure, M₃T_{1.4} exhibited the best performance on the overall degradation of RhB in the aqueous system. The results also indicated that high TiO₂ content leads to catalyst aggregation, which lowers active sites, and reduces light penetration, and scattering [13].

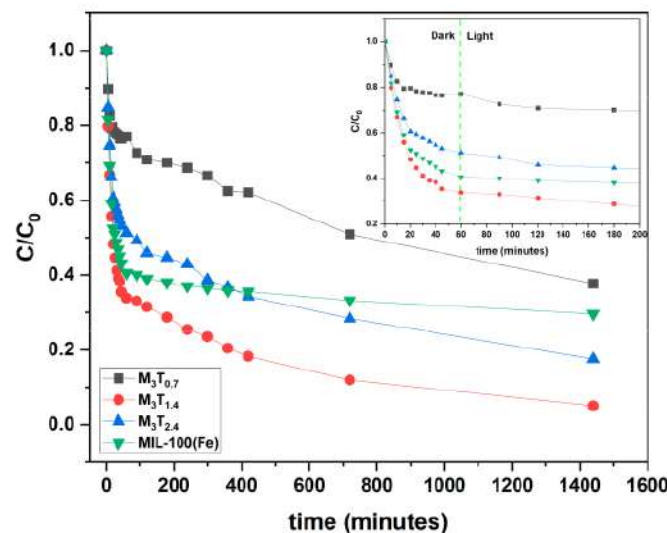


Figure 15. Effect of TiO_2 ratio towards RhB adsorption and photocatalytic degradation.

3.4.3. Effect of Fenton Addition

Adding Fenton reagent (H_2O_2) to the process can enhance the number of $\bullet\text{OH}$ species while lowering the radiation intensity, energy consumption, and cost-effectiveness. This phenomenon was studied by adding various amounts of Fenton (1 mL, 2 mL, and 3 mL) into the system containing 100 ppm of RhB and 50 mg of $\text{M}_3\text{T}_{1.4}$ adsorbent. The photocatalytic degradation process in this research was performed by radiating the solution with the visible LED light after adsorption. The rate constant of the degradation process was determined by non-linear fitting of the experimental data, as shown in Figure 16. Based on the non-linear fitting in Table 8, first-order kinetics suited the experimental data better than the second-order and BMG model kinetics. From the synthesized materials, $\text{M}_3\text{T}_{1.4}$ exhibited the highest rate constant (k_{1p}), compared with the others. Based on the result shown in Figure 17, adding a small amount of Fenton improved the photodegradation ability, as shown in Figure 17 and Table 9. As previously mentioned, there are three possible ways in which Fenton could create a sufficient amount of $^{\circ}\text{OH}$ radicals: (i) it obtains electrons from $^{\circ}\text{O}_2^-$ radicals to make the $^{\circ}\text{OH}$ radicals; (ii) it reduces H_2O_2 at the band conduction to produce $^{\circ}\text{OH}$ radicals, which prevent photo-generated electrons and holes from recombination; or (iii) $^{\circ}\text{OH}$ radicals are produced when visible light irradiation causes self-degradation. As a result of these actions, the oxidation rate is accelerated, and the removal efficiency is increased [27].

3.4.4. Reusability Test

The reusability potential of the composite was investigated in this study for five cycles of adsorption–photodegradation of RhB. The experiments were conducted as follows: after adsorption–photodegradation, the adsorbent was soaked in ethanol (24 h), and centrifuged, then dried at 55°C for 6 h. Subsequently, the adsorbent was used in the next cycle. Based on the results shown in Figure 18, the removal percentage of the RhB slightly decreased after five cycles, indicating the stability of composite as the adsorbent.

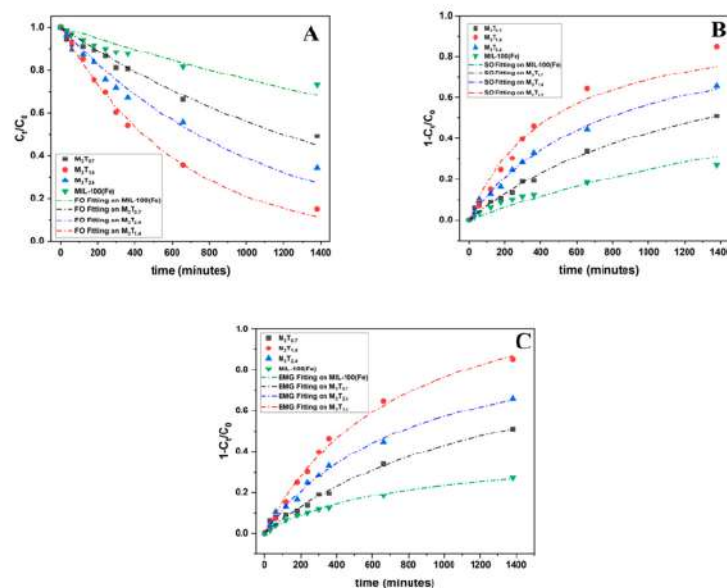


Figure 16. (A) FO kinetic fittings on each component; (B) SO kinetic fitting on each component; (C) BMG kinetic fittings on each component.

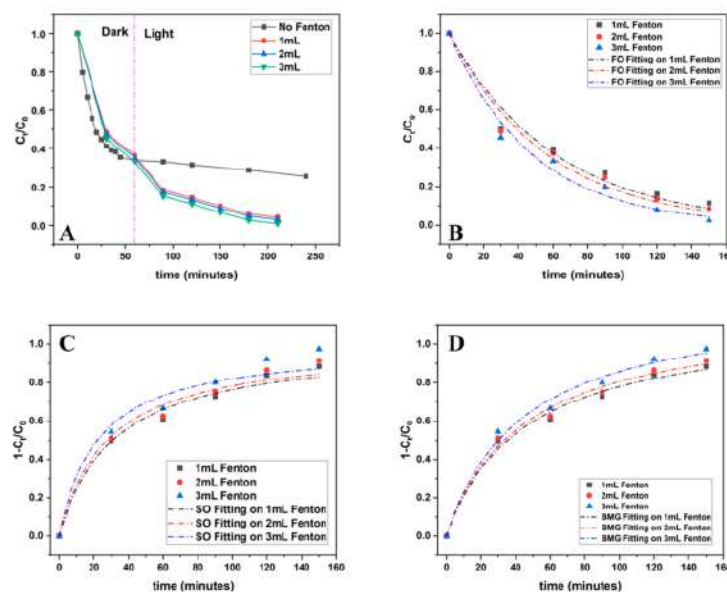
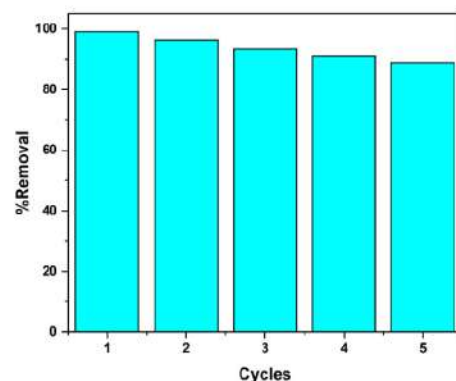


Figure 17. (A) Effect of each Fenton volume towards RhB adsorption and photocatalytic degradation (B) FO kinetic fittings on each Fenton volume; (C) SO kinetic fittings on each Fenton volume; (D) BMG kinetic fittings on each Fenton Volume.

Table 9. Photocatalytic degradation kinetic reaction.

Kinetic Reaction Model	Technical Constant ^a	Catalyst and LED Irradiation without Fenton				Catalyst and LED Irradiation with Fenton on M ₃ T _{1.4}		
		M ₃ T _{0.7}	M ₃ T _{1.4}	M ₃ T _{2.4}	MIL-100(Fe)	1 mL	2 mL	3 mL
First-order kinetics $C_t = C_0 \exp(-k_1 t)$	$k_1 \times 10^3 \text{ (min}^{-1}\text{)}$	0.5834	1.5700	0.9479	0.2793	16.32	17.68	20.84
	R^2	0.9847	0.9944	0.9829	0.9462	0.9914	0.9964	0.9925
Second-order kinetics $1 - \frac{C_t}{C_0} = \frac{k_2 I}{1 + k_2 I}$	$k_2 \times 10^3 \text{ (L} \cdot \text{mg}^{-1} \cdot \text{min}^{-1}\text{)}$	0.7483	2.2100	1.3100	0.3305	32.43	36.17	45.56
	R^2	0.9830	0.9666	0.9629	0.9039	0.9842	0.9795	0.9659
$1 - \frac{BMG}{C_0} = \frac{t}{m + bt}$	$m \text{ (min)}$	1353.4	568.115	783.069	1819.64	39.26	38.02	35.69
	b	0.9767	0.7399	0.9663	2.4655	0.8896	0.8615	0.8088
	R^2	0.9809	0.9829	0.9832	0.9249	0.9811	0.9891	0.9885

^a Calculated based on non-linear fitting on Origin Pro 2021 Software (Northampton, MA, USA).

Figure 18. Stability and reusability of M₃T_{1.4}.

3.5. Plausible Mechanism of Photocatalytic Degradation of RhB on M_xT_y

During photocatalytic degradation, many active species are involved in the process, such as photoinduced hydroxyl radicals (OH^*), superoxide anion radicals (O_2^{*-}), and electron holes (h^+). Free radical scavenging experiments were conducted to confirm the existence of these active species inside the system. Isopropanol (IP), benzoquinone (BQ), ammonium oxalate (AO), and sodium azide (SA) were prepared with a concentration of 0.001 M as scavengers for OH^* , O_2^{*-} , h^+ , and O_2 , respectively. RhB degradation was decreased and hindered with the presence of BQ and IP (Figure 19A). RhB only slightly degraded with the addition of AO and SA. The arrangement of total degradation was determined based on the influence of each free radical scavenger: BQ > IP > AO > SA > no scavenger. Briefly, this experiment concluded that the crucial O_2^{*-} active species played a crucial role in the mechanism of RhB degradation.

From the UV-Vis DRS characterization in Table 3, a high band gap value of MIL-100(Fe) (5.35 eV) may restrict the excitation of the electron processes, which decreases its capability in photocatalytic degradation. However, the M₃T_{1.4} composite exhibited the lowest band gap energy value (3.26 eV) compared with the other ratios, including its precursor (pristine MIL-100(Fe) and TiO₂ anatase). These results showed that the M₃T_{1.4} composite successfully improved the photocatalytic degradation capability, corresponding to its lower band gap value. Therefore, a plausible mechanism of photocatalytic degradation has been shown (in Figure 19B), with the further explanation as follows: (1) visible light irradiation gives sufficient energy for the electrons (e^-) from MIL-100's conduction band to jump/migrate into the TiO₂'s conduction band; (2) the excitation of the electrons creates holes (h^+) on the TiO₂'s valence band, which then migrate into the MIL-100(Fe)'s valence band; (3) this repeating

process allows photo-excited electrons (e^-) and holes (h^+) to contact with oxygen and water molecules, respectively; (4) after contact with photo-excited electrons and holes, oxygen molecules create $O_2^{\bullet -}$ while water molecules create OH^{\bullet} [8]; (5) these free radicals will then degrade the organic pollutant and turn it into mineralization products, such as carbon dioxide and water.

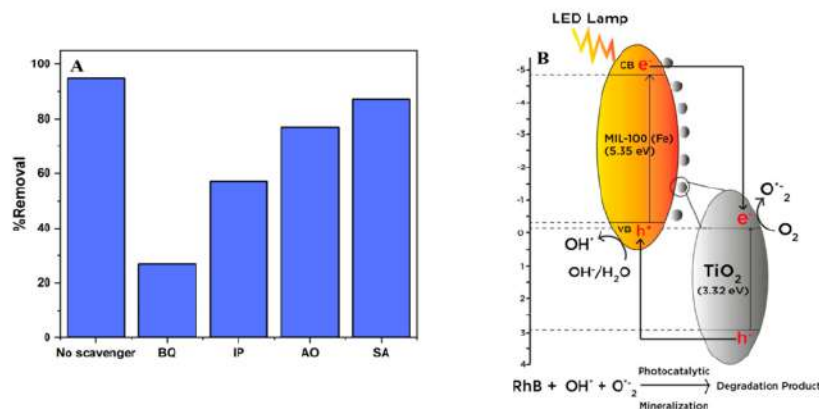


Figure 19. (A) Free radicals scavenging experiment on overall degradation; (B) plausible mechanism of photocatalytic degradation of RhB towards M_xT_y .

4. Conclusions

In summary, an effective and efficient photocatalyst composite was successfully synthesized via a simple hydrothermal method from MIL-100(Fe) and a TiO_2 anatase precursor. Characterization of the synthesized M_xT_y proved to be quite successful and provided enough evidence to conclude that the materials will have high photocatalytic performances. This was confirmed with the aforementioned adsorption–photocatalytic degradation experiment results, in which the optimal composite ($M_3T_{1.4}$) degraded the organic RhB pollutant to 99%. The addition of Fenton was also proven to be successful in increasing the photocatalytic abilities of the synthesized materials. The synthesized materials were also found to have good reusability.

Author Contributions: Conceptualization, S.I., F.E.S., and V.B.L.; Formal analysis, J.N.P., S.P.S., J.L., H.S. and H.A.; Investigation, P.A. and C.J.W.; Methodology, V.B.L., M.Y., W.I. and P.A.; Validation, S.I., I.G.W., and F.E.S.; Writing—original draft, P.A. and V.B.L.; Writing—review & editing, S.I., J.N.P., S.P.S. All 7 authors have read and agreed to the published version of the manuscript.

Funding: This research was funded by the Directorate of Research and Community Service, Deputy for Strengthening Research and Development, Ministry of Culture and Education, Research and Technology, Number: 260C/WM01.5/N/2022.

Institutional Review Board Statement: Not applicable.

Informed Consent Statement: Not applicable.

Data Availability Statement: All data have been given in this manuscript.

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Al-Maythah, B.A.; Shekha, O.; Swaidan, R.; Belmabkhout, Y.; Pinnau, I.; Eddaoudi, M. Quest for anionic MOF membranes: Continuous sod-ZMOF membrane with CO_2 adsorption-driven selectivity. *J. Am. Chem. Soc.* **2015**, *137*, 1754–1757. [CrossRef] [PubMed]
2. Lu, G.; Chu, F.; Huang, X.; Li, Y.; Liang, K.; Wang, G. Recent advances in Metal-Organic Frameworks-based materials for photocatalytic selective oxidation. *Coord. Chem. Rev.* **2022**, *450*, 214240. [CrossRef]

3. Wang, M.; Yang, L.; Guo, C.; Liu, X.; He, L.; Song, Y.; Zhang, Q.; Qu, X.; Zhang, H.; Zhang, Z.; et al. Bimetallic Fe/Ti-Based Metal–Organic Framework for Persulfate-Assisted Visible Light Photocatalytic Degradation of Orange II. *ChemistrySelect* **2018**, *3*, 3664–3674. [\[CrossRef\]](#)
4. Ai, L.; Zhang, C.; Li, L.; Jiang, J. Iron terephthalate metal-organic framework: Revealing the effective activation of hydrogen peroxide for the degradation of organic dye under visible light irradiation. *Appl. Catal. B Environ.* **2014**, *148–149*, 191–200. [\[CrossRef\]](#)
5. Li, X.; Guo, W.; Liu, Z.; Wang, R.; Liu, H. Fe-based MOFs for efficient adsorption and degradation of acid orange 7 in aqueous solution via persulfate activation. *Appl. Surf. Sci.* **2016**, *369*, 130–136. [\[CrossRef\]](#)
6. Liu, N.; Huang, W.; Zhang, X.; Tang, L.; Wang, L.; Wang, Y.; Wu, M. Ultrathin graphene oxide encapsulated in uniform MIL-88A(Fe) for enhanced visible light-driven photodegradation of RhB. *Appl. Catal. B Environ.* **2018**, *221*, 119–128. [\[CrossRef\]](#)
7. Ke, F.; Wang, L.; Zhu, J. Facile fabrication of CdS-metal-organic framework nanocomposites with enhanced visible-light photocatalytic activity for organic transformation. *Nano Res.* **2015**, *8*, 1834–1846. [\[CrossRef\]](#)
8. Huang, J.; Song, H.; Chen, C.; Yang, Y.; Xu, N.; Ji, X.; Li, C.; You, J.A. Facile synthesis of N-doped TiO₂ nanoparticles caged in MIL-100(Fe) for photocatalytic degradation of organic dyes under visible light irradiation. *J. Environ. Chem. Eng.* **2017**, *5*, 2579–2585. [\[CrossRef\]](#)
9. He, X.; Fang, H.; Gosztola, D.J.; Jiang, Z.; Jena, P.; Wang, W.N. Mechanistic Insight into Photocatalytic Pathways of MIL-100(Fe)/TiO₂ Composites. *ACS Appl. Mater. Interfaces* **2019**, *11*, 12516–12524. [\[CrossRef\]](#)
10. Liu, L.; Liu, Y.; Wang, X.; Hu, N.; Li, Y.; Li, C.; Meng, Y.; An, Y. Synergistic effect of B-TiO₂ and MIL-100(Fe) for high-efficiency photocatalysis in methylene blue degradation. *Appl. Surf. Sci.* **2021**, *561*, 149969. [\[CrossRef\]](#)
11. Kondamareddy, K.K.; Neena, D.; Lu, D.; Peng, T.; Lopez MA, M.; Wang, C.; Yu, Z.; Cheng, N.; Fu, D.J.; Zhao, X.Z. Ultra-trace (parts per million-ppm) W 6+ dopant ions induced anatase to rutile transition (ART) of phase pure anatase TiO₂ nanoparticles for highly efficient visible light-active photocatalytic degradation of organic pollutants. *Appl. Surf. Sci.* **2018**, *456*, 676–693. [\[CrossRef\]](#)
12. Horcajada, P.; Surlé, S.; Serre, C.; Hong, D.Y.; Seo, Y.K.; Chang, J.S.; Grenèche, J.M.; Margiolaki, I.; Férey, G. Synthesis and catalytic properties of MIL-100(Fe), an iron(III) carboxylate with large pores. *Chem. Commun.* **2007**, *100*, 2820–2822. [\[CrossRef\]](#)
13. Angela, S.; Bervia Lunardi, V.; Kusuma, K.; Edi Soetaredjo, F.; Nyoo Putro, J.; Permatasari Santoso, S.; Elisa Angkawijaya, A.; Lie, J.; Gunarto, C.; Kurniawan, A.; et al. Facile Synthesis of Hierarchical Porous ZIF-8@TiO₂ for Simultaneous Adsorption and Photocatalytic Decomposition of Crystal Violet. *Environ. Nanotechnol. Monit. Manag.* **2021**, *16*, 100598. [\[CrossRef\]](#)
14. Guo, S.; Chi, L.; Zhao, T.; Nan, Y.; Sun, X.; Huang, Y.; Hou, B.; Wang, X. Construction of MOF/TiO₂ nanocomposites with efficient visible-light-driven photocathodic protection. *J. Electroanal. Chem.* **2021**, *880*, 114915. [\[CrossRef\]](#)
15. Zheng, J.; Liu, Z.; Liu, X.; Yan, X.; Li, D.; Chu, W. Facile hydrothermal synthesis and characteristics of B-doped TiO₂ hybrid hollow microspheres with higher photocatalytic activity. *J. Alloy. Compd.* **2011**, *509*, 3771–3776. [\[CrossRef\]](#)
16. Xu, J.; Xu, J.; Jiang, S.; Cao, Y.; Xu, K.; Zhang, Q.; Wang, L. Facile synthesis of a novel Ag₃PO₄/MIL-100(Fe) Z-scheme photocatalyst for enhancing tetracycline degradation under visible light. *Environ. Sci. Pollut. Res.* **2020**, *27*, 37839–37851. [\[CrossRef\]](#)
17. Tian, H.; Araya, T.; Li, R.; Fang, Y.; Huang, Y. Removal of MC-LR using the stable and efficient MIL-100/MIL-53 (Fe) photocatalyst: The effect of coordinate immobilized layers. *Appl. Catal. B Environ.* **2019**, *254*, 371–379. [\[CrossRef\]](#)
18. Wei, Y.; Cheng, G.; Xiong, J.; Xu, F.; Chen, R. Positive Ni(HCO₃)₂ as a Novel Cocatalyst for Boosting the Photocatalytic Hydrogen Evolution Capability of Mesoporous TiO₂ Nanocrystals. *ACS Sustain. Chem. Eng.* **2017**, *5*, 5027–5038. [\[CrossRef\]](#)
19. Giles, C.H.; MacEwan, T.H.; Nakhwa, S.N.; Smith, D. Studies in Adsorption. Part XI. A System. *J. Chem. Soc.* **1960**, *846*, 3973–3993. [\[CrossRef\]](#)
20. Bonilla-Petriciolet, A.; Mendoza-Castillo, D.I.; Reynel-Ávila, H.E. Adsorption processes for water treatment and purification. In *Adsorption Processes for Water Treatment and Purification*; Springer: Berlin/Heidelberg, Germany, 2017. [\[CrossRef\]](#)
21. Lima, E.C.; Hosseini-Bandegharaei, A.; Moreno-Piraján, J.C.; Anastopoulos, I. A critical review of the estimation of the thermodynamic parameters on adsorption equilibria. Wrong use of equilibrium constant in the Van't Hoff equation for calculation of thermodynamic parameters of adsorption. *J. Mol. Liq.* **2019**, *273*, 425–434. [\[CrossRef\]](#)
22. Karmakar, S.; Roy, D.; Janiak, C.; De, S. Insights into multi-component adsorption of reactive dyes on MIL-101-Cr metal-organic framework: Experimental and modeling approach. *Sep. Purif. Technol.* **2019**, *215*, 259–275. [\[CrossRef\]](#)
23. Yadav, S.; Asthana, A.; Singh, A.K.; Chakraborty, R.; Vidya, S.S.; Susan, M.A.B.H.; Carabineiro, S.A. Adsorption of cationic dyes, drugs and metal from aqueous solutions using a polymer composite of magnetic/β-cyclodextrin/activated charcoal/Na alginate: Isotherm, kinetics and regeneration studies. *J. Hazard. Mater.* **2021**, *409*, 124840. [\[CrossRef\]](#) [\[PubMed\]](#)
24. Biggar, J.; Cheung, M. Adsorption of picloram (4-amino-3,5,6-trichloropicolinic acid) on panoche, ephrata, and palouse soils: A thermodynamic approach to the adsorption mechanism. *Soil Sci. Soc. Am. J.* **1973**, *37*, 863–868. [\[CrossRef\]](#)
25. Khan, A.A.; Singh, R. Adsorption thermodynamics of carbofuran on Sn(IV) arsenosilicate in H⁺, Na⁺ and Ca²⁺ forms. *Colloids Surf.* **1987**, *24*, 33–42. [\[CrossRef\]](#)
26. Milonjić, S.K. A consideration of the correct calculation of thermodynamic parameters of adsorption. *J. Serbian Chem. Soc.* **2007**, *72*, 1363–1367. [\[CrossRef\]](#)
27. Hejazi, R.; Mahjoub, A.R.; Khavar AH, C.; Khazaei, Z. Fabrication of novel type visible-light-driven TiO₂@MIL-100 (Fe) microspheres with high photocatalytic performance for removal of organic pollutants. *J. Photochem. Photobiol. A Chem.* **2020**, *400*, 112644. [\[CrossRef\]](#)

ORIGINALITY REPORT

24%

SIMILARITY INDEX

13%

INTERNET SOURCES

21%

PUBLICATIONS

5%

STUDENT PAPERS

PRIMARY SOURCES

1

repository.globethics.net

Internet Source

2%

2

Xin Liu, Rui Dang, Wenjun Dong, Xiubing Huang, Jia Tang, Hongyi Gao, Ge Wang. "A sandwich-like heterostructure of TiO₂ nanosheets with MIL-100(Fe): A platform for efficient visible-light-driven photocatalysis", *Applied Catalysis B: Environmental*, 2017

Publication

1%

3

Submitted to University of Portsmouth

Student Paper

1%

4

Valentino Bervia Lunardi, Felycia Edi Soetaredjo, Kuncoro Foe, Jindrayani Nyoo Putro et al. "Pesticide Elimination through Adsorption by Metal-Organic Framework and Their Modified Forms", *Environmental Nanotechnology, Monitoring & Management*, 2022

Publication

1%

5

Lu Liu, Yang Liu, Xingguo Wang, Nan Hu, Yan Li, Cheng Li, Yu Meng, Yonglei An. "Synergistic

1%

effect of B-TiO₂ and MIL-100(Fe) for high-efficiency photocatalysis in methylene blue degradation", Applied Surface Science, 2021

Publication

6

Submitted to University of Limerick

Student Paper

1 %

7

Jindrayani Nyoo Putro, Felycia Edi Soetaredjo, Wenny Irawaty, Sandy Budi Hartono et al.

"Cellulose Nanocrystals (CNCs) and Its Modified Form from Durian Rind as Dexamethasone Carrier", Polymers, 2022

Publication

1 %

8

econpapers.repec.org

Internet Source

1 %

9

pubs.rsc.org

Internet Source

<1 %

10

www.tandfonline.com

Internet Source

<1 %

11

Raheleh Hejazi, Ali Reza Mahjoub, Amir Hossein Cheshme Khavar, Zeynab Khazaei.

"Fabrication of novel type visible-light-driven TiO₂@MIL-100 (Fe) microspheres with high photocatalytic performance for removal of organic pollutants", Journal of Photochemistry and Photobiology A: Chemistry, 2020

Publication

<1 %

12

Yuanyuan Li, Jun Jiang, Yu Fang, Zhenlei Cao, Dongyun Chen, Najun Li, Qingfeng Xu, Jianmei Lu. " TiO Nanoparticles Anchored onto the Metal–Organic Framework NH -MIL-88B(Fe) as an Adsorptive Photocatalyst with Enhanced Fenton-like Degradation of Organic Pollutants under Visible Light Irradiation ", ACS Sustainable Chemistry & Engineering, 2018

Publication

<1 %

13

Jia-Yan Pu, Xiu-Tong Wang, Jing-Quan Liu, Mei-Peng Ren et al. "PDA decorated spaced TiO₂ nanotube array photoanode material for photocathodic protection of 304 stainless steels", Journal of Electroanalytical Chemistry, 2022

Publication

<1 %

14

Asma Hamed, Francesco Trotta, Mahmood Borhani Zarandi, Marco Zanetti et al. "In Situ Synthesis of MIL-100(Fe) at the Surface of Fe₃O₄@AC as Highly Efficient Dye Adsorbing Nanocomposite", International Journal of Molecular Sciences, 2019

Publication

<1 %

15

Chao-Wei Huang, Shi-Rong Zhou, Wen-Chieh Hsiao. "Multifunctional TiO₂/MIL-100(Fe) to conduct adsorption, photocatalytic, and heterogeneous photo-Fenton reactions for

<1 %

removing organic dyes", Journal of the Taiwan Institute of Chemical Engineers, 2023

Publication

16

Yanan Wei, Bingfeng Wang, Xinfang Cui, Yaseen Muhammad, Yanjuan Zhang, Zuqiang Huang, Xuesheng Li, Zhenxia Zhao, Zhongxing Zhao. "Highly Advanced Degradation of Thiamethoxam by Synergistic Chemisorption-Catalysis Strategy Using MIL(Fe)/Fe-SPC Composites with Ultrasonic Irradiation", ACS Applied Materials & Interfaces, 2018

Publication

<1 %

17

coek.info

Internet Source

<1 %

18

Hairus Abdullah, Noto Susanto Gultom, Hardy Shuwanto, Worku Lakew Kebede, Dong-Hau Kuo. "Self-protonated Ho-doped Zn(O,S) as a green-chemical-conversion catalyst to hydrogenate nitro to amino compounds", ACS Applied Materials & Interfaces, 2020

Publication

<1 %

19

shura.shu.ac.uk

Internet Source

<1 %

20

vdoc.pub

Internet Source

<1 %

21

Teresa Aguilar, Javier Navas, Desireé M De los Santos, Antonio Sánchez-Coronilla et al. " TiO

<1 %

and pyrochlore Tm Ti O based semiconductor as a photoelectrode for dye-sensitized solar cells ", Journal of Physics D: Applied Physics, 2015

Publication

22

scholarscompass.vcu.edu

Internet Source

<1 %

23

pubs.acs.org

Internet Source

<1 %

24

Tingting Geng, Jie He, Lifang Hu, Jie Li.
"Structure and photocatalytic oxidation
desulfurization performance of
CeO₂/HTi₂NbO₇-NS nanocomposite",
Inorganic Chemistry Communications, 2019

Publication

<1 %

25

Submitted to Swinburne University of
Technology

Student Paper

<1 %

26

lutpub.lut.fi

Internet Source

<1 %

27

ujcontent.uj.ac.za

Internet Source

<1 %

28

Shella Permatasari Santoso, Artik Elisa
Angkawijaya, Alfin Kurniawan, Maria Yuliana
et al. "Utilization of Nanocrystalline Cellulose
for Adsorption of Divalent Cobalt Ions in the

<1 %

29

Hairus Abdullah, Noto Susanto Gultom, Hardy Shuwanto, Worku Lakew Kebede, Dong-Hau Kuo. "Self-Protonated Ho-Doped Zn(O,S) as a Green Chemical-Conversion Catalyst to Hydrogenate Nitro to Amino Compounds", ACS Applied Materials & Interfaces, 2020

Publication

<1 %

30

Sara Khan, Qing Guan, Qian Liu, Zewan Qin, Bilal Rasheed, Xiaoxia Liang, Xia Yang. "Synthesis, modifications and applications of MILs Metal-organic frameworks for environmental remediation: The cutting-edge review", Science of The Total Environment, 2022

Publication

<1 %

31

Yong-Xuan Hou, Hairus Abdullah, Dong-Hau Kuo, Sy-Jye Leu, Noto Susanto Gultom, Chi-Hung Su. "A comparison study of SiO₂ /nano metal oxide composite sphere for antibacterial application", Composites Part B: Engineering, 2018

Publication

<1 %

32

hdl.handle.net

Internet Source

<1 %

33

Chaoyue Wang, Peng Lv, Daxiang Xue, Yun Cai, Xiaoxiao Yan, Lin Xu, Jun Fang, Yang Yang. "0D/2D Au₂₅(Cys)₁₈ Nanoclusters/g-C₃N₄ Nanosheets Composites for Enhanced Photocatalytic Hydrogen Production under Visible Light", ACS Sustainable Chemistry & Engineering, 2018

Publication

<1 %

34

Liang Kong, Junqiu Guo, Joshua W. Makepeace, Tiancun Xiao, Heather F. Greer, Wuzong Zhou, Zheng Jiang, Peter P. Edwards. "Rapid synthesis of BiOBr_xI_{1-x} photocatalysts: Insights to the visible-light photocatalytic activity and strong deviation from Vegard's Law", Catalysis Today, 2019

Publication

<1 %

35

Qiangshun Wu, Muhammad Saboor Siddique, Yuling Guo, Mi Wu, Yuankun Yang, Hanpei Yang. "Low-crystalline bimetallic metal-organic frameworks as an excellent platform for photo-Fenton degradation of organic contaminants: Intensified synergism between hetero-metal nodes", Applied Catalysis B: Environmental, 2021

Publication

<1 %

36

Rimeh Daghrir, Patrick Drogui, Didier Robert. "Modified TiO₂ For Environmental Photocatalytic Applications: A Review ",

<1 %

37

Sanjoy K. Maji, Sheng-Wei Wang, Chen-Wuing Liu. "Arsenate removal from aqueous media on iron-oxide-coated natural rock (IOCNR): a comprehensive batch study", Desalination and Water Treatment, 2013

Publication

<1 %

38

Susanginee Nayak, K. M. Parida. " Dynamics of Charge-Transfer Behavior in a Plasmon-Induced Quasi-Type-II p-n/n-n Dual Heterojunction in Ag@Ag PO /g-C N /NiFe LDH Nanocomposites for Photocatalytic Cr(VI) Reduction and Phenol Oxidation ", ACS Omega, 2018

Publication

<1 %

39

Yanying He, Dongbo Wang, Xiaopei Li, Qizi Fu, Linmiao Yin, Qi Yang, Hong Chen. "Photocatalytic degradation of tetracycline by metal-organic frameworks modified with Bi₂WO₆ nanosheet under direct sunlight", Chemosphere, 2021

Publication

<1 %

40

Hai Nguyen Tran, Sheng-Jie You, Ahmad Hosseini-Bandegharaei, Huan-Ping Chao. "Mistakes and inconsistencies regarding adsorption of contaminants from aqueous

<1 %

41

Mohammad Mansoob Khan, Ashmalina Rahman, Shaidatul Najihah Matussin. "Recent Progress of Metal-Organic Frameworks and Metal-Organic Frameworks-Based Heterostructures as Photocatalysts", Nanomaterials, 2022

Publication

<1 %

42

Xiang He, Hong Fang, David J. Gosztola, Zhang Jiang, Puru Jena, Wei-Ning Wang. "Mechanistic Insight into Photocatalytic Pathways of MIL-100(Fe)/TiO Composites ", ACS Applied Materials & Interfaces, 2019

Publication

<1 %

43

scholarsjunction.msstate.edu

Internet Source

<1 %

44

Chen Chen, Shi Quan. "RSU Cluster Deployment and Collaboration Storage of IoV Based Blockchain", Sustainability, 2022

Publication

<1 %

45

Livy Laysandra, Immanuel Joseph Ondang, Yi-Hsu Ju, Benedikta Hervina Ariandini et al. "Highly adsorptive chitosan/saponin-bentonite composite film for removal of methyl orange and Cr(VI)", Environmental Science and Pollution Research, 2019

<1 %

46

Nan Zhang, Yanhui Zhang, Xiaoyang Pan, Xianzhi Fu, Siqi Liu, Yi-Jun Xu. "Assembly of CdS Nanoparticles on the Two-Dimensional Graphene Scaffold as Visible-Light-Driven Photocatalyst for Selective Organic Transformation under Ambient Conditions", The Journal of Physical Chemistry C, 2011

Publication

<1 %

47

Y. Yamamoto. "Mapping vegetable area with spectral mixture analysis of the Landsat-ETM", IEEE International Geoscience and Remote Sensing Symposium IGARSS-02, 2002

Publication

<1 %

48

static.frontiersin.org

Internet Source

<1 %

49

Araya, Tirusew, Manke Jia, Jian Yang, Ping Zhao, Kuan Cai, Wanhong Ma, and Yingping Huang. "Resin modified MIL-53 (Fe) MOF for improvement of photocatalytic performance", Applied Catalysis B Environmental, 2016.

Publication

<1 %

50

Miaoyan Huang, Juncao Bian, Wei Xiong, Chao Huang, Rui-Qin Zhang. "Low-dimensional Mo:BiVO₄ photoanodes for enhanced photoelectrochemical activity", Journal of Materials Chemistry A, 2018

Publication

<1 %

51	Miriam Appiah-Brempong, Helen Michelle Korkor Essandoh, Nana Yaw Asiedu, Gabriel Ntoni, Francis Yao Momade. "Removal of Colour and COD from vegetable tannery wastewater onto bone char– Effect of process parameters, adsorption mechanism, kinetics and equilibrium modelling", Separation Science and Technology, 2023 Publication	<1 %
52	Salameh, Y.. "Kinetic and thermodynamic investigations on arsenic adsorption onto dolomitic sorbents", Chemical Engineering Journal, 20100601 Publication	<1 %
53	Submitted to University of Newcastle Student Paper	<1 %
54	edoc.hu-berlin.de Internet Source	<1 %
55	iwaponline.com Internet Source	<1 %
56	Desheng Liu, Pan Jiang, Xiaochun Li, Jianxi Liu, Lincheng Zhou, Xiaolong Wang, Feng Zhou. "3D printing of metal-organic frameworks decorated hierarchical porous ceramics for high-efficiency catalytic degradation", Chemical Engineering Journal, 2020 Publication	<1 %

57

Gabriela Peña-Velasco, Laura Hinojosa-Reyes, Gerardo Arturo Morán-Quintanilla, Aracely Hernández-Ramírez et al. "Synthesis of heterostructured catalyst coupling MOF derived Fe₂O₃ with TiO₂ for enhanced photocatalytic activity in anti-inflammatory drugs mixture degradation", *Ceramics International*, 2021

Publication

<1 %

58

Jinbei Yang, Shuyue Yu, Wentao Chen, Yibing Chen. "Rhodamine B removal from aqueous solution by CT269DR resin: Static and dynamic study", *Adsorption Science & Technology*, 2019

Publication

<1 %

59

Vania Bundjaja, Tirta Mutiara Sari, Felycia Edi Soetaredjo, Maria Yuliana et al. "Aqueous sorption of tetracycline using rarasaponin-modified nanocrystalline cellulose", *Journal of Molecular Liquids*, 2020

Publication

<1 %

60

Wu, Luoming, Jing Xiao, Ying Wu, Shikai Xian, Guang Miao, Haihui Wang, and Zhong Li. "A Combined Experimental/Computational Study on the Adsorption of Organosulfur Compounds over Metal–Organic Frameworks from Fuels", *Langmuir*, 2014.

Publication

<1 %

61

Yohannis Fetene, Taffere Addis. "Adsorptive Removal of Phosphate From Wastewater Using Ethiopian Rift Pumice: Batch Experiment", Air, Soil and Water Research, 2020

Publication

<1 %

62

bmcchem.biomedcentral.com

Internet Source

<1 %

63

Huang, Y.. "Ultrasonic spray pyrolysis synthesis and visible light activity of carbon-doped TiO₂/ZrO₂ solid solution photocatalysts", Materials Chemistry & Physics, 20090315

Publication

<1 %

64

Lu Chen, Xiao Wang, Zepeng Rao, Zixia Tang, Yan Wang, Gansheng Shi, Guanhong Lu, Xiaofeng Xie, Deliang Chen, Jing Sun. "In-situ Synthesis of Z-Scheme MIL-100(Fe)/ α -Fe₂O₃ Heterojunction for Enhanced Adsorption and Visible-light Photocatalytic Oxidation of O-xylene", Chemical Engineering Journal, 2021

Publication

<1 %

65

Poonam Benjwal, Kamal K. Kar. "Simultaneous photocatalysis and adsorption based removal of inorganic and organic impurities from water by titania/activated carbon/carbonized epoxy nanocomposite", Journal of Environmental Chemical Engineering, 2015

<1 %

66 Siyuan Wang, Hua Yang, Gang Hu, Wangjun Feng. " Synthesis and enhanced photocatalytic activity of Cu(OH) cluster modified Bi WO toward RhB degradation ", Materials Technology, 2018

Publication

<1 %

67 SpringerBriefs in Molecular Science, 2015.

Publication

<1 %

68 Submitted to University of Technology, Sydney

Student Paper

<1 %

69 Wen-Jun Luo, Qiang Gao, Xiao-Liang Wu, Cheng-Gang Zhou. "Removal of Cationic Dye (Methylene Blue) from Aqueous Solution by Humic Acid-Modified Expanded Perlite: Experiment and Theory", Separation Science and Technology, 2014

Publication

<1 %

70 Xianwei Fan, Ran Zhao, Haoxuan Hu, Junyi Liu, Yahui Nie, Dong Wang. " In-situ preparation of MIL-88A(Fe)/MIL-100(Fe)/PVA-Co-PE nanofiber membranes for efficient photocatalytic reduction of CO ", IOP Conference Series: Earth and Environmental Science, 2021

Publication

<1 %

71 pure.tue.nl

Internet Source

<1 %

72

Jie Huang, Haiyan Song, Chunxia Chen, Yi Yang, Ningdi Xu, Xinzheng Ji, Chunyu Li, Jiang-An You. "Facile synthesis of N-doped TiO₂ nanoparticles caged in MIL-100(Fe) for photocatalytic degradation of organic dyes under visible light irradiation", Journal of Environmental Chemical Engineering, 2017

Publication

<1 %

73

Juan Li, Liangjie Wang, Yongqiang Liu, Ping Zeng, Yan Wang, Yizhang Zhang. "Removal of Berberine from Wastewater by MIL-101(Fe): Performance and Mechanism", ACS Omega, 2020

Publication

<1 %

74

Kumar, A.. "Adsorption of phenol and 4-nitrophenol on granular activated carbon in basal salt medium: Equilibrium and kinetics", Journal of Hazardous Materials, 20070817

Publication

<1 %

75

Li-Yun Guo, Hai-Qin Lu, Darryn Rackemann, Changrong Shi, Wen Li, Kai Li, William O.S. Doherty. "Quaternary ammonium-functionalized magnetic chitosan microspheres as an effective green adsorbent to remove high-molecular-weight invert sugar alkaline degradation products (HISADPs)", Chemical Engineering Journal, 2021

Publication

<1 %

76

Maria Yuliana, Suryadi Ismadji, Jenni Lie, Shella Permatasari Santoso et al. "Low-cost structured alginate-immobilized bentonite beads designed for an effective removal of persistent antibiotics from aqueous solution", *Environmental Research*, 2022

Publication

<1 %

77

Roozbeh Soltani, Azam Marjani, Reza Soltani, Saeed Shirazian. "Hierarchical multi-shell hollow micro-meso-macroporous silica for Cr(VI) adsorption", *Scientific Reports*, 2020

Publication

<1 %

78

Sanjoy Kumar Maji, Anjali Pal, Tarasankar Pal. "Arsenic removal from real-life groundwater by adsorption on laterite soil", *Journal of Hazardous Materials*, 2008

Publication

<1 %

79

Shunhong Dong, Juan Wu, Lanlan Huang, Hong-En Wang. "Pt-Modified Interfacial Engineering for Enhanced Photocatalytic Performance of 3D Ordered Macroporous TiO₂", *Crystals*, 2022

Publication

<1 %

80

Yarui Wang, Wanchao Yu, Fanglan Geng, Lixia Zhao, Yawei Wang. "TiO₂@MOF Photocatalyst for the Synergetic Oxidation of Microcystin-LR and Reduction of Cr(VI) in Aqueous Media", *Catalysts*, 2021

<1 %

81	Yu Zou, Bozhi Ren, Zhendong He, Xinping Deng. "Enhanced Removal of Sb (III) by Hydroxy-Iron/Acid-Base-Modified Sepiolite: Surface Structure and Adsorption Mechanism", Water, 2022 Publication	<1 %
----	---	------

82	bibliotekanauki.pl Internet Source	<1 %
----	---	------

83	discovery.ucl.ac.uk Internet Source	<1 %
----	---	------

84	jultika.oulu.fi Internet Source	<1 %
----	---	------

85	mostwiedzy.pl Internet Source	<1 %
----	---	------

86	repository.mut.ac.ke:8080 Internet Source	<1 %
----	---	------

87	Anica Dadwal, Vishal Mishra. "Review on Biosorption of Arsenic From Contaminated Water", CLEAN - Soil, Air, Water, 2017 Publication	<1 %
----	--	------

88	Cláudio Pereira Jordão. "A Study on Al(III) and Fe(II) Ions Sorption by Cattle Manure Vermicompost", Water Air and Soil Pollution, 10/02/2009 Publication	<1 %
----	--	------

89

Hamza Ahmad Isiyaka, Khairulazhar Jumbri, Nonni Soraya Sambudi, Zakariyya Uba Zango, Bahruddin Saad, Adamu Mustapha. "Removal of 4-chloro-2-methylphenoxyacetic acid from water by MIL-101(Cr) metal-organic framework: kinetics, isotherms and statistical models", Royal Society Open Science, 2021

Publication

<1 %

90

Padmesh, T.V.N.. "Application of Azolla rongpong on biosorption of acid red 88, acid green 3, acid orange 7 and acid blue 15 from synthetic solutions", Chemical Engineering Journal, 20060901

Publication

<1 %

91

Shafaei, A.. "Equilibrium studies of the sorption of Hg(II) ions onto chitosan", Chemical Engineering Journal, 20070915

Publication

<1 %

92

Weidong Mei, Hui Song, Ziyi Tian, Shiyu Zuo, Dongya Li, Haiming Xu, Dongsheng Xia. "Efficient photo-Fenton like activity in modified MIL-53(Fe) for removal of pesticides: Regulation of photogenerated electron migration", Materials Research Bulletin, 2019

Publication

<1 %

93

core.ac.uk
Internet Source

<1 %

94

ebin.pub

Internet Source

<1 %

95

sipac.ufgd.edu.br

Internet Source

<1 %

96

teacher.scu.edu.cn

Internet Source

<1 %

97

www.coudert.name

Internet Source

<1 %

98

Hai Nguyen Tran, Sheng-Jie You, Huan-Ping Chao. "Thermodynamic parameters of cadmium adsorption onto orange peel calculated from various methods: A comparison study", Journal of Environmental Chemical Engineering, 2016

Publication

<1 %

99

Sumei Li, Saisai Shan, Sha Chen, Li Hanbing, Ziyi Li, Yixuan Liang, Jiaying Fei, Linhua Xie, Jianrong Li. "Photocatalytic Degradation of Hazardous Organic Pollutants in Water by Fe-MOFs and Their Composites: A Review", Journal of Environmental Chemical Engineering, 2021

Publication

<1 %

100

Tadeja Birsa Čelič, Mojca Rangus, Károly Lázár, Venčeslav Kaučič, Nataša Zabukovec Logar. "Spectroscopic Evidence for the

<1 %

Structure Directing Role of the Solvent in the Synthesis of Two Iron Carboxylates", Angewandte Chemie, 2012

Publication

-
- 101 Unuabonah, E.I.. "Adsorption of lead and cadmium ions from aqueous solutions by tripolyphosphate-impregnated Kaolinite clay", Colloids and Surfaces A: Physicochemical and Engineering Aspects, 20070115

Publication

-
- 102 Zakariyya Uba Zango, Khairulazhar Jumbri, Nonni Soraya Sambudi, Anita Ramli et al. "A Critical Review on Metal-Organic Frameworks and Their Composites as Advanced Materials for Adsorption and Photocatalytic Degradation of Emerging Organic Pollutants from Wastewater", Polymers, 2020

Publication

-
- 103 ir.lib.uwo.ca

Internet Source

-
- 104 Dongfang Zhang. "Chemical synthesis of Ni/TiO₂ nanophotocatalyst for UV/visible light assisted degradation of organic dye in aqueous solution", Journal of Sol-Gel Science and Technology, 2011

Publication

-
- 105 Fu Li, Yongchun Dong, Weimin Kang, Bowen Cheng, Guixin Cui. "Enhanced removal of azo

dye using modified PAN nanofibrous membrane Fe complexes with adsorption/visible-driven photocatalysis bifunctional roles", Applied Surface Science, 2017

Publication

106 Jianchao Zhan, Hui Zhang, Guoqing Zhu. <1 %
"Magnetic photocatalysts of cenospheres coated with Fe₃O₄/TiO₂ core/shell nanoparticles decorated with Ag nanopartilces", Ceramics International, 2014

Publication

107 Kurniawan, Alfin, Chintya Effendi, Lu Ki Ong, <1 %
Yi-Hsu Ju, Chun Xiang Lin, and Suryadi Ismadji. "Novel, Integrated Biorefinery Approach of Ceiba pentandra (Kapok) Seed and Its Secondary Waste", ACS Sustainable Chemistry & Engineering, 2013.

Publication

108 Martin Reli, Pengwei Huo, Marcel Šihor, Nela <1 %
Ambrožová et al. " Novel TiO₂ /C N Photocatalysts for Photocatalytic Reduction of CO and for Photocatalytic Decomposition of N₂O ", The Journal of Physical Chemistry A, 2016

Publication

109 Thi Kim Ngan Tran, Cao Phuong Khanh Phan, <1 %
Thi Cam Quyen Ngo, Ngoc Bich Hoang, Le Dang Truong, Thi Kim Oanh Nguyen.

"Synthesis and Characterization Bimetallic Organic Framework CoxFex(BDC) and Adsorption Cationic and Anionic Dyes", Processes, 2022

Publication

-
- 110 Valentino Bervia Lunardi, Felycia Edi Soetaredjo, Jindrayani Nyoo Putro, Shella Permatasari Santoso et al. "Nanocelluloses: Sources, Pretreatment, Isolations, Modification, and Its Application as the Drug Carriers", Polymers, 2021 <1 %
- Publication
-
- 111 Xianghui Li, Weilin Guo, Xiaomei Gao, Xinxin Yue. "Phosphotungstic acid encapsulated in MIL-53(Fe) as efficient visible-light photocatalyst for rhodamine B degradation", Environmental Progress & Sustainable Energy, 2017 <1 %
- Publication
-

Exclude quotes Off

Exclude matches Off

Exclude bibliography On